

# The Potential of Biomass-Based Activated Carbon to Remove Heavy Metals in Wastewater – A Review

*by* Vina Rofikoh

---

**Submission date:** 04-Jul-2023 09:07AM (UTC+0700)

**Submission ID:** 2126234421

**File name:** Artikel\_Publikasi\_\_Vina\_Rofikoh\_\_JIL.docx (589.82K)

**Word count:** 6100

**Character count:** 35688

## The Potential of Biomass-Based Activated Carbon to Remove Heavy Metals in Wastewater – A Review

Vina Rofikoh<sup>1</sup>, Badrus Zaman<sup>2</sup>, Budi Prasetyo Samadikun<sup>2</sup>

<sup>1</sup>Master Program of Environmental Engineering, Diponegoro University-Semarang Indonesia; e-mail: [rofikohvina@gmail.com](mailto:rofikohvina@gmail.com)

<sup>2</sup>Dept. of Environmental Engineering, Faculty of Engineering, Diponegoro University-Semarang, Indonesia.

### ABSTRAK

Karbon aktif komersial ialah jenis adsorben yang sering digunakan dalam proses adsorpsi. Namun, penggunaan dari karbon komersial dalam pengolahan air limbah dibatasi, karena terbatasnya ketersediaan prekursor dan harganya cukup mahal. Biomassa sebagai prekursor karbon aktif telah dilaporkan memiliki efisiensi yang tinggi dalam menghilangkan berbagai macam logam berat dalam air limbah. Review ini bertujuan untuk membahas potensi karbon aktif berbasis biomassa untuk mengadsorpsi logam berat dalam hal komponen penyusun biomassa, penyisihan logam berat, dan prospek dimasa depan. Hasil penelitian menunjukkan bahwa karbon aktif berbasis biomassa efektif dalam menyisihkan logam berat dalam berbagai jenis air limbah. Efektivitas penyisihan untuk berbagai jenis biomassa berkisar antara 84 – 99% untuk ion Pb<sup>2+</sup>, 55 – 92% untuk ion Cd<sup>2+</sup>, 84 – 99% untuk ion Pb<sup>2+</sup>, 96% untuk ion As<sup>2+</sup>, 80 – 100% untuk ion Cr<sup>2+</sup>, 25 – 97% untuk ion Fe<sup>2+</sup>, 50 – 99% untuk ion Ni<sup>2+</sup>, dan 62 – 98% untuk ion Cu<sup>2+</sup>, serta 98% untuk ion Ti. Hasil ini menunjukkan bahwa logam berat memiliki afinitas yang berbeda-beda terhadap karbon aktif dari biomassa, dari semua logam berat, ion Fe<sup>2+</sup> dan Cd<sup>2+</sup> memiliki afinitas yang terendah, sehingga karbon aktif yang digunakan untuk menghilangkan logam Fe<sup>2+</sup> dan Cd<sup>2+</sup> perlu diproduksi dengan porositas dan luas permukaan yang lebih tinggi. Penyisihan logam berat menggunakan karbon aktif dari biomassa dibatasi oleh beberapa faktor, yang meliputi dosis adsorbent, waktu kontak, pH larutan, temperatur, konsentrasi awal adsorbat, ukuran partikel dan kecepatan pengadukan. Pada penelitian selanjutnya diharapkan adanya karbon aktif dari biomassa yang mempunyai kapasitas adsorpsi tinggi, biaya ekonomis, ramah lingkungan dan dapat digunakan dalam skala yang lebih luas.

**Kata kunci:** Karbon aktif, Biomassa, Logam berat, Lignoselulosa, Pengolahan air limbah.

### ABSTRACT

Commercial activated carbon is a type of adsorbent commonly used in adsorption processes. However, the use of commercial carbon in wastewater treatment is still limited, due to the scarce availability of precursors and their high cost. Biomass as an activated carbon precursor has been reported to have high efficiency in removing various heavy metals in wastewater. This review aims to discuss the potential of biomass-based activated carbon to adsorb heavy metals in terms of biomass constituent components, heavy metal removal, and prospects. The results show that biomass-based activated carbon is effective in the removal of heavy metals in various types of wastewater. The removal effectiveness for different types of biomass ranged from 84 - 99% for Pb<sup>2+</sup> ions, 55 - 92% for Cd<sup>2+</sup> ions, 84 - 99% for Pb<sup>2+</sup> ions, 96% for As<sup>2+</sup> ions, 80 - 100% for Cr<sup>2+</sup> ions, 25 - 97% for Fe<sup>2+</sup> ions, 50 - 99% for Ni<sup>2+</sup> ions, and 62 - 98% for Cu<sup>2+</sup> ions, and 98% for Ti ions. These results show that heavy metals have different affinities to activated carbon from biomass, from all heavy metals, Fe<sup>2+</sup> and Cd<sup>2+</sup> ions have the lowest affinity, so the activated carbon used to remove Fe<sup>2+</sup> and Cd<sup>2+</sup> metals needs to be produced with higher porosity and surface area. The removal of heavy metals using activated carbon from biomass is limited by several factors, including adsorbent dosage, contact time, solution pH, temperature, initial adsorbate concentration, particle size, and stirring speed. In future research, it is expected that activated carbon from biomass has a high adsorption capacity, is economical cost, is environmentally friendly and can be used on a larger scale.

**Keywords:** Activated carbon, Biomass, Heavy metals, Lignocellulose, Wastewater treatment.

**Citation:** Pertama, S., Kedua, P., dan Akhir, P. (Tahun). Judul. Jurnal Ilmu Lingkungan, xx(x), xx-xx, doi:10.14710/jil.xx.xxx-xx

## 1. Introduction

Heavy metals are pollutants produced by various industries, including the textile, dyeing, batteries, leather, fertilizer, chemical, mining, metallurgy, and refinery. The heavy metals such as Cd, Cu, Zn, Pb, Fe, Hg, Ni, Mn, and Co are commonly found in small concentrations of industrial wastewater but are considered elements harmful to living beings (Zhou et al., 2020), as these metals are not biodegradable and highly toxic. Metals adsorbed and accumulated in the human body can cause cancer, tumours, brain diseases, psychiatric diseases, sexual diseases and so on (Shafiq et al., 2018).

Various materials are offered as adsorbents, but activated carbon is an accepted material for removing pollutants in wastewater. In removing heavy metals from wastewater, activated carbon has long been recognized as the best adsorbent in the industry (Lu et al., 2014). Applying the adsorption method with activated carbon was chosen because it is relatively easy. Compared to other adsorbents, activated carbon has a very high surface area and capacity for adsorption, making its use more optimal (Gunawan et al., 2020). Several different carbonaceous materials can be used to make activated carbon, but until recently, the primary sources of commercial carbon were coal, anthracite, and bitumen (Saleem et al., 2019).

The precursor materials of commercial activated carbon, such as petroleum waste, coal, asphalt, and lignite used in commercial activated carbon production, are expensive and non-renewable (Yahya et al., 2015). The availability of such precursors is limited (Elavarasan, 2018), and the cost required for commercial activated carbon regeneration is expensive (Ali et al., 2012). High production costs and expensive materials limit their use in wastewater treatment. Alternatively, locally available, abundant in nature and renewable materials, such as biomass, can be modified physically and chemically as activated carbon (Azmi et al., 2014). Biomass is a term for waste material from plants, animals, and other organic

substances. Biomass is a non-lignocellulose or lignocellulose material that comes in many shapes and sizes, including wood, herbs, aquatic detritus, manure and byproducts, and other forms (Osman et al., 2019).

Lignocellulose biomass has gained significant attention as the only abundant renewable energy source with many ecological benefits (Bu et al., 2015). Lignocellulose biomass is made from photosynthesis of various types of land plants or aquatic plants (Long et al., 2013). Lignocellulosic biomass is the ideal feedstock for making activated carbon as it is the only renewable source of green carbon. In addition, lignocellulose biomass also has high adsorption capacity, simple regeneration, abundant availability, low cost, and reduced disposal problems after adsorption (Khatoon & Rai, 2016). Therefore, lignocellulose biomass is affordable, and sustainable alternative to manufacture activated carbon. In addition, biomass-based activated carbon can be adapted for various purposes (Pallarés et al., 2018). The advantages and disadvantages of commercial and biomass-based activated carbon are present in Table 1. Biomass-based activated carbon has many advantages over commercial carbon. However, recent studies have shown that the activation of biomass-based activated carbon uses large acid doses (Kolur et al., 2019). So, the effluent from the activated carbon treatment will contaminate the sewer system and stop the hydrolysis process in the environment (Bakar et al., 2021).

Many researchers have utilized lignocellulose biomass as activated carbon to remove heavy metals in wastewater. The biomass includes banana peels (Ajmi et al., 2018), soybean seeds (Gaur et al., 2018), neem leaves (Pournima & Shrikant, 2018), olive seeds and palm seeds (Obregón-Valencia & Sun-Kou, 2014), and *Leucaena leucocephala* seed pods (Yusuff, 2019). Therefore, this review article summarizes studies about the potential of lignocellulose biomass-based activated carbon for removing heavy metals in wastewater.

**Table 1.** Advantages and disadvantages of commercial and biomass-based activated carbon

Activated Carbon	Advantages	Disadvantages
Commercial	<ul style="list-style-type: none"><li>• Easy to find</li><li>• High adsorption capacity</li></ul>	<ul style="list-style-type: none"><li>• Limited precursor availability</li><li>• High price</li><li>• The cost of regeneration is expensive</li></ul>
Biomass	<ul style="list-style-type: none"><li>• High adsorption capacity</li><li>• Abundant precursor availability</li><li>• Economical cost</li><li>• Easy regeneration</li><li>• Less disposal problems after adsorption</li></ul>	<ul style="list-style-type: none"><li>• Acidic waste from activated carbon activation causes contamination of drainage systems and disrupts biodegradation cycles.</li></ul>

## 2. Biomass-Based Activated Carbon

### 2.1. Constituent Components of Biomass-Based Activated Carbon

Amorphous materials are called activated carbons, usually containing a well-organized tissue of pores with a high proportion of micro or mesopores structural. Due to its naturally connected pore

network, lignocellulosic biomass is a highly applicable precursor for producing porous activated carbon (Dutta et al., 2014). Lignocellulose biomass has hollow holes and plates connecting vertical and horizontal pores. This network of pores plays an essential role in transferring plant nutrients so that they can transport

anorganic ions and nutritional components (Jiang et al., 2020).

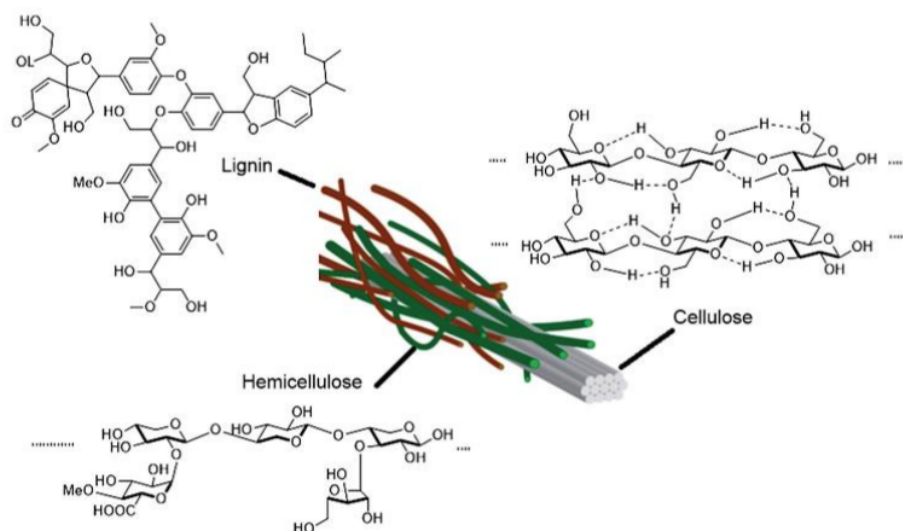


Figure 1. Structural elements of lignocellulose biomass (Li & Takkellapati, 2018)

According to (Karaboyaci et al., 2017), lignocellulose biomass comprises three main components: lignin, cellulose, and hemicellulose. The structural elements constituent of lignocellulose biomass is illustrated in Figure 1. Lignin is essential in absorbing heavy metals from raw or unaltered lignocellulose biomass. Escudero-Oñate et al. (2017) state that lignin is crucial for adsorption because it supplies polyphenol and polyhydroxy functional elements that are helpful for heavy metal coordination and promote ion exchange activity in materials. It is also part of the lignocellulose biomass that is most thermally stable. Due to these properties, lignin-rich biomass is suitable for producing the best-activated carbon.

According to Escudero-Oñate et al. (2017), adsorbents of lignocellulose have a proportion of 30–35% cellulose, 20–40% hemicellulose and 15–25% lignin. The ash, waters, cyclic hydro-carbons, and extractive are other micro-components. According to Kayranli et al. (2021), the banana peel contains lignin 16.45%, cellulose 18.06%, hemicellulose 21.40%, crude protein 1.4%, fibre 10.56%, and ash 4.5%. Sugar bagasse's lignocellulose composition is 36.78% cellulose, 26.04% hemicellulose, 10.51% lignin, and 26.67% ash (Arni, 2018). Rice husks are composed of cellulose 35%, hemicellulose 25%, lignin 20%, and ash 17%. (Ma'ruf et al., 2017). Watermelon peel contains lignin 6–8.63%, cellulose 52.27% and hemicellulose 10.14–19.51% (Fakayode et al., 2021). Potato peels contain 39.36% cellulose components, 13.11% lignin, 9.04% hemicellulose, and 2.31% pectin (Zhu et al., 2023). 75–90% of rice husk biomass is organic matter (cellulose and lignin), while 10–25% is organic (Carmona et al., 2013). Adsorbents from

chemically treated biomass have a much greater adsorption ability than non-treated adsorbents (Ali et al., 2013). Adsorbents from chemically treated biomass have a much greater adsorption ability than non-treated adsorbents. According to (Pournima & Shrikant, 2018), Cu metal can be removed from wastewater by silica, cellulose, lignin, carbohydrate, and other biomass components. Biomass offers many benefits, such as a cheap feedstock to replace commercial carbon and as a problem-solving component for removing heavy metals from wastewater.

## 2.2. Biomass-Based Activated Carbon Applications

Lignocellulosic biomass has a high potential as an activated carbon precursor. Biomass-based activated carbon can adsorb various heavy metals in wastewater. Biomass-based activated carbon has been applied in various experiments to remove metal contaminants easily and cheaply (Burakov et al., 2018). Table 2 details the use of activated carbon derived from several types of biomass for wastewater treatment.

Based on the summary in Table 2, activated carbon based on lignocellulosic biomass can remove different heavy metals in wastewater. The biomass derived from several plant parts reportedly can be used as an activated carbon precursor. Previous experiments have reported the removal of heavy metals by plant biomass, such as leaves, stems, seeds, and fruit peels. Lead metal (Pb) can be reduced using activated carbon from aloe vera leaves, bamboo stems, corn cobs, cherry seeds, apricot shells, potato

peels, and banana peels, with an effectiveness of 84-99%.

**Table 2.** Wastewater treatment using activated carbon from biomass.

Part of plant	Biomass	Types of wastewater	Heavy metals	Effectiveness	Reference	
Leaf	Aloe Vera Leaf	Wastewater	Pb <sup>2+</sup>	96%	Malik et al. (2015)	
Stems	Bamboo sticks	Oil and gas industry wastewater	Cd <sup>2+</sup>	55%	Thotagamuge et al. (2021)	
			Pb <sup>2+</sup>	96%		
			As <sup>2+</sup>	96%		
			Cr <sup>2+</sup>	96%		
			Fe <sup>2+</sup>	25%		
			Ni <sup>2+</sup>	50%		
	Rice straw	Wastewater	Cr <sup>2+</sup>	97%	Kumar & Jena (2017)	
	Sugar bagasse	Wastewater Textile industry	Fe <sup>2+</sup>	91%	Razi et al. (2018)	
			Zn <sup>2+</sup>	89%		
Fruit	Corn cobs	Wastewater Leather industry	Pb <sup>2+</sup>	95%	Muthusamy & Murugan (2016)	
Seed	Black sapote seeds	Mining wastewater	Cr <sup>2+</sup>	100%	Peláez-Cid et al. (2020)	
			Cu <sup>2+</sup>	98%		
			Fe <sup>2+</sup>	96%		
	Apricot shell	Wastewater		Pb <sup>2+</sup>	99%	Šoštarić et al. (2018)
				Fe <sup>2+</sup>	97%	
				Pb <sup>2+</sup>	87%	
				Cu <sup>2+</sup>	81%	
				Cr <sup>2+</sup>	80%	
	Cherry seeds	Wastewater		Pb <sup>2+</sup>	94%	Vukelic et al. (2018)
				Cd <sup>2+</sup>	92%	
	Peels	Olive seeds	Wastewater	Ni <sup>2+</sup>	66%	Obregón-Valencia & Sun-Kou (2014)
		Palm seeds	Wastewater	Cd <sup>2+</sup>	68%	
		Banana peels	Battery and power industry wastewater	Cd <sup>2+</sup>	55%	Ajmi et al. (2018)
				Cr <sup>2+</sup>	98%	
		Potato peels	Wastewater	Cr <sup>2+</sup>	99%	Osman et al. (2019)
Watermelon peel		Wastewater	Pb <sup>2+</sup>	97%		
Watermelon peel		Wastewater	Pb <sup>2+</sup>	84%	Li et al. (2019)	
Rice husks		Synthetic wastewater	Ti	98%		
Rice husks and orange peels				Cu <sup>2+</sup>	98%	Gupta & Gogate (2016)
				Ni <sup>2+</sup>	62%	
	Ni <sup>2+</sup>			65%		
Rice husks	Tannery Wastewater		Cu <sup>2+</sup>	99%	Vunain et al. (2021)	
			Ni <sup>2+</sup>	99%		

The significance of removing cadmium (Cd) with activated carbon from bamboo stems, olive seeds and palms, and banana peels was 55-98%. Activated carbon from bamboo sticks can remove arsenic (As) from oil and gas industry wastewater with an effectiveness of 96% (Thotagamuge et al., 2021). Chromium (Cr) metal from various wastewater types can remove by activated carbon from bamboo stems, rice straws, black sapote seeds, apricot fruit peels, banana peels, and rice husks with an effectiveness of 80-100%. Removal of iron (Fe) from wastewater with activated carbon from bamboo stems, bagasse, black sapote seeds, and apricot shells, the effectiveness ranged from 25-97%. Nickel (Ni) can remove by activated carbon from bamboo stems, cherry seeds, rice husks and orange peels with an effectiveness of 50-99%. 8% (27) of the zinc (Zn) metal was successfully removed from textile effluent using sugarcane bagasse-derived activated carbon (Razi et al., 2018). Copper (Cd) in wastewater can be removed by activated carbon from black sapote seeds, apricot shells, watermelon peels, rice husks and orange peels, with an effectiveness of 62-99%. Meanwhile, titanium (Ti) metal in wastewater can be removed with

watermelon pe<sup>6</sup>-activated carbon with 98% effectiveness (Li et al., 2019). According to Vukelic et al. (2018), commercial activated carbon can remove 87% nickel metal, 84% cadmium and 74% lead in wastewater. In a study by Thotagamuge et al. (2021), commercial activated carbon can remove 58% (14) u, 15% Cd, Pb, and Cr, 10% As and Ni in wastewater fr<sup>39</sup> the oil and gas industry. These results indicate that the removal efficiency of heavy metals in wastewater with plant biomass-based activated carbon (lignocellulose) is equal to or even higher than commercial activat<sup>4</sup> carbon. Thus, biomass is a potential precursor as activated carbon for heavy metal removal in wastewater.

## 2.3. Limiting Factors

### 2.3.1 Adsorbent Dosage

The quantity of adsorbent used in removing heavy metal is significant because it determines the balance between adsorbent materials and contaminants, which estimates the adsorption p<sup>9</sup>ce for each unit of solution (Mohamed et al., 2019). The number of heavy metal ions adsorbed usually increases with increased adsorbent dosage up to a

certain point before becoming constant. This result indicates that maximum adsorption will occur at a given adsorbent dose for each concentration of metal ions (Soliman & Moustafa, 2020).

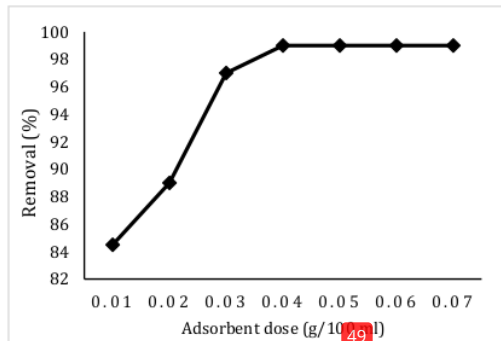


Figure 2. Impact of adsorbent dose on Cr(VI) removal by activated carbon from peanut shell (Kumar & Jena, 2017)

The increase in adsorbent dosage significantly increases active sites, surface area, and the number of metal ions adsorbed. For example, Kumar & Jena, 2017 investigated the impact of the adsorbent dosage on removing Cu, Cr, and Pb using peanut shell activated carbon (Fig. 2). The percentage removal of Cr(VI) increased sharply by increasing the dose of adsorbent until 0.04 before constant. Meanwhile, according to Özsin et al. (2019), the removal of adsorbed metals decreased as the dose of carbon increased. The adsorbent dose of lead (Pb) was found to be optimal at 2 g/L, while copper (Cu) and chromium (Cr) were optimal at 3 g/L.

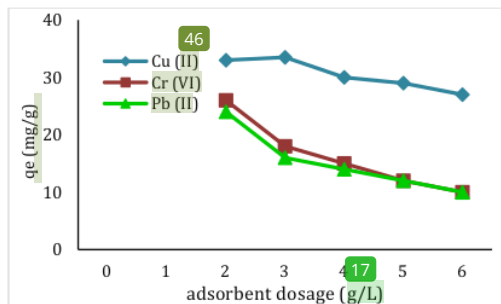


Figure 3. Impact of adsorbent dose on sorption of Cu, Cr, and Pb metal by chickpea peel activated carbon (Özsin et al., 2019)

### 2.3.2 Contact Time

Contact time is the period it takes for the system to reach equilibrium. Solid or liquid heterogeneous systems typically undergo various mass transfer processes, some of which may be relatively slow. With a longer contact time, the biosorption of heavy metals may increase (Khatoun dan Rai, 2016). Activated carbon from papaya peel is used by Mittal et al. (2021) to study the impact of contact duration on the removal of Pb(II), Ni(II), and Cu(II) ions (Fig. 4). The number of heavy metal ions adsorbed over time of all

three metals starts quickly but slows down with time, and no adsorption of metal ions is visible once equilibrium is reached. Metal ions can first fill the adsorption site. However, as time passes, fewer free sites become available, and the amount of unadsorbed cations in the solution increases, limiting the adsorption capacity (Bohli et al., 2015).

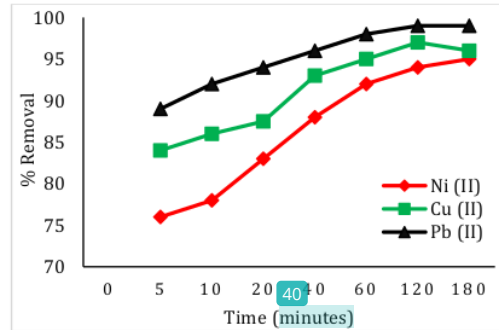


Figure 4. Impact of contact time on the metal ion sorption by papaya peel carbon (Mittal et al., 2021).

### 2.3.3 Solution pH

Solution pH significantly impacts the adsorption in heavy metals, as pH controls an adsorbent's properties, including the surface charges, specifications of the adsorbate and the ionization level in the solution (Alghamdi et al., 2019). Figure 5 illustrates more protons on the carbon surface interacting with the metal ions of the solution. When pH rises, lead (Pb), copper (Cu), and chromium (Cr) adsorption increase. Metal adsorption decreases at pH > 9, possibly related to a binding or dissociation of functional groups on the surface. In addition, the change in pH of the solution from 8 to 10 does not significantly change the absorption rate (Özsin et al., 2019).


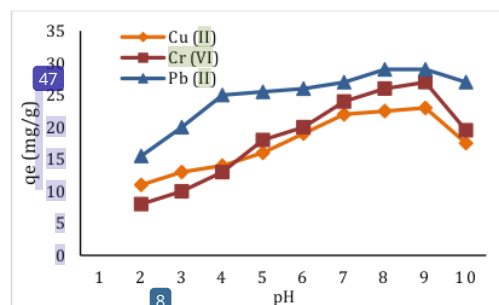


Figure 5. Impact of the solution pH on the sorption of Pb, Cr, and Cu metals (Özsin et al., 2019)

### 2.3.4 Temperature

Temperature can change the nature of the interaction between endothermic and exothermic systems or the reverse, which impacts adsorption (Yeow et al., 2021). The absorption efficiency is influenced by temperature, depending on the

pollutants and adsorbents. Temperature can increase surface activity and adsorbate kinetic energy leading to increased biosorption of contaminants, but temperature can also damage the physical structure of biosorbents (Rápó & Tonk, 2021). Al-Senani & Al-Fawzan (2018) investigated how temperature affected the sorption of metal ions Li, Co and Cd using equisetum (EH) and Teucrium (TH) adsorbents (figure 6). The adsorption of Cd, Co, and Li metals is affected by temperatures in the range of 25-60°C. Adsorbents may absorb heavy metal ions through physical and chemical adsorption, as evidenced by the increasing adsorption with temperature variations. Mustapha et al. (2019) report that the adsorption rate reduces as the temperature rises. These results indicate that adsorption becomes negative at high temperatures (desorption).

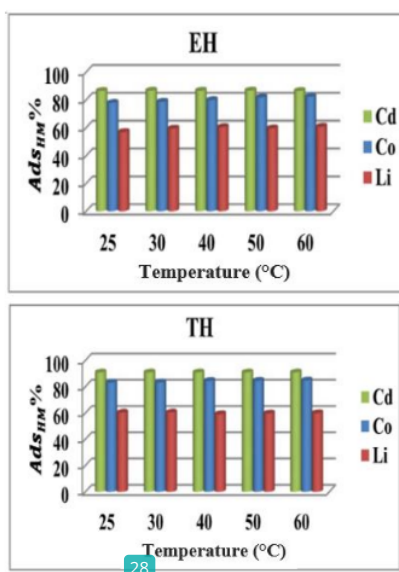

28  
Figure 6. The impact of temperature on the removal of metal ions by Equisetum (EH) and Teucrium (TH) adsorbents (Al-Senani & Al-Fawzan, 2018)

### 2.3.5 Initial Adsorbate Concentration

The initial concentration of adsorbate determines the ability of the biosorbent for adsorbate uptake. The initial concentration impacts the adsorbate's absorption, which increases as the initial concentration rises. An increase in the pushing gradient force causes changes in biosorption at different adsorbate concentrations. The driving force for moving adsorbate is more potent at higher concentrations. However, the binding site will be saturated at high metal concentrations (Alkherraz et al., 2020). The adsorption sites available are filled with increasing concentrations of heavy metals, followed by decreased adsorption effectiveness. The effect of initial heavy metal concentration on metal adsorption by carbon from pine and Silver birch has

been investigated by Komkiene & Baltreinaite (2016). Findings showed that the percentage of adsorption decreases with increasing initial metal concentration.

### 2.3.6 Particle Size/Surface Area

30  
An adsorbent's particle size significantly impacts its ability to absorb pollutants (Al-Ghouti et al., 2017). As a result, the lower surface area, the adsorbent's increasing particle size causes a decrease in its adsorption characteristics. However, reducing the particle size of the adsorbent will increase its adsorptive properties as the surface area improves (Bohli et al., 2013). Particle size was investigated by Holliday et al. (2022), using particles measuring 200-500, 50-200, and 50 µm in adsorption. According to the findings, adsorption works best when using small particles (50 m). Smaller particle sizes can increase the interface's ratio to volume and the number of accessible adsorption sites.

### 2.3.7 Speed of Agitation

Agitation is a crucial factor in adsorption because agitation allows the adsorbent to overcome the mass transfer resistance of the boundary layer (Khatoun & Rai, 2016). Increased agitation speed facilitates the mass transfer and transport of contaminated molecules. The increased surface contact promotes faster equilibration and more significant adsorption. The solids will sink to the bottom of the solution without agitation, decreasing the potential number of sites for absorption (Holliday et al., 2022). The effect of agitation speed toward metal ions removal from solution was investigated in the study Salih et al. (2021), using 100, 150 and 200 rpm speeds. Studies show that when the agitation speed increases, the effectiveness of metal removal also rises.

## 3. Future Perspective

35  
Many studies have highlighted the potential of using lignocellulosic biomass as an activated carbon precursor to treat heavy metals from wastewater. Activated carbon made from biomass-based lignocellulose can be utilized commercially as an alternative to carbon in the future due to the abundant availability of precursors, economical price and high adsorption capacity. Therefore, further research should focus on filling the following gaps:

- 1) Further studies are needed to characterize activated carbons from lignocellulose biomass with the highest heavy metal absorption capacity to encourage the large-scale use of biomass-based activated carbons.
- 2) Various pre-processing techniques must be explored to make activated carbon efficient during heavy metal remediation.
- 3) Chemical activation processes have been widely used to manufacture biomass-based activated carbon. Although it produces quality activated carbon, it produces acidic wastewater that can

pollute the environment. Future carbon-based biomass activation requires improvement not to produce byproducts that negatively impact the environment.

- 4) Despite the many studies conducted regarding the production of various biomasses as activated carbon, a more profound and more extensive range of carbon synthesis and modification methodologies is still needed, mainly focusing on each more specific type of biomass.
- 5) As a result of several studies focusing on activated carbon production from biomass, more research is needed to determine the feasibility of biomass-based carbon reuse. Since actual wastewater not only contains heavy metals but also contains a complex range of pollutants and most studies have focused solely on activated carbon on a laboratory scale, further research on a broad scale is urgently needed.

#### 4. Conclusion

Lignocellulose biomass-based activated carbon has been reported as a promising commercial carbon substitute alternative. This biomass-based carbon can adsorb various types of heavy metals in wastewater. The benefits of lignocellulose biomass-based carbon over commercial carbon include being relatively affordable, renewable, available, simple to modify, and having a high adsorption capacity. The constituent components of lignocellulose biomass as carbon precursors include lignin, cellulose and hemicellulose. Biomass from plant parts can set aside different types of metals. Aloe vera leaves can remove  $Pb^{2+}$  metal in wastewater with 96% effectiveness. Activated carbon from plant stems in bamboo stems, rice straw, and bagasse can remove metals  $Cd^{2+}$ ,  $Pb^{2+}$ ,  $As^{2+}$ ,  $Cr^{2+}$ ,  $Fe^{2+}$ ,  $Ni^{2+}$  and  $Zn^{2+}$  in various wastewater by 25–97%. Corn cob, the activated carbon from the plant's fruit, can remove up to 95% of  $Pb^{2+}$  metal. Activated carbon from grains, such as black persimmons, cherries, olives, palms, and apricot shells, can set aside metals  $Cd^{2+}$ ,  $Fe^{2+}$ ,  $Pb^{2+}$ ,  $Cu^{2+}$ ,  $Cr^{2+}$ , and  $Ni^{2+}$  ranging from 55–100%. The effectiveness of removing  $Cd^{2+}$ ,  $Pb^{2+}$ ,  $Cu^{2+}$ ,  $Cr^{2+}$ , and  $Ni^{2+}$  metals by activated carbon from banana, watermelon, potato, rice husk and orange peels is 62–99%. The benefits of removing heavy metals with activated carbon made from lignocellulosic biomass are excellent; some biomass from plant parts even excels in commercial carbon. The amount of heavy metals activated carbon can remove depends on several variables, including the adsorbent dose, contact time, solution pH, temperature, initial adsorbate concentration, particle size, and agitation speed. In future research, it is expected that there will be biomass-based activated carbon that has high metal adsorption capacity, lower economic costs, free of pollution, and can be applied on a wide scale.

#### DAFTAR PUSTAKA

- Ajmi, R. A., Sultan, M., & Hanno, S. H. (2018). Bioadsorbent of Chromium, Cadmium and Lead from Industrial waste water by Waste plant. *Journal of Pharmaceutical Sciences and Research*, 10(3), 672–674.
- Alghamdi, A. A., Al-Odayni, A. B., Saeed, W. S., Al-Kahtani, A., Alharthi, F. A., & Aouak, T. (2019). Efficient adsorption of lead (II) from aqueous phase solutions using polypyrrole-based activated carbon. *Materials*, 12(12). <https://doi.org/10.3390/ma12122020>
- Al-Ghouti, M. A., Al-Disi, Z. A., Al-Kaabi, N., & Khraisheh, M. (2017). Mechanistic insights into the remediation of bromide ions from desalinated water using roasted date pits. *Chemical Engineering Journal*, 308, 463–475. <https://doi.org/10.1016/j.cej.2016.09.091>
- Ali, A., Saeed, K., & Mabood, F. (2016). Removal of chromium (VI) from aqueous medium using chemically modified banana peels as efficient low-cost adsorbent. *Alexandria Engineering Journal*, 55(3), 2933–2942. <https://doi.org/10.1016/j.aej.2016.05.011>
- Ali, I., Asim, M., & Khan, T. A. (2012). Low-cost adsorbents for the removal of organic pollutants from wastewater. In *Journal of Environmental Management* (Vol. 113, pp. 170–183). <https://doi.org/10.1016/j.jenvman.2012.08.028>
- Alkherraz, A. M., Ali, A. K., & Elsherif, K. M. (2020). Removal of  $Pb(II)$ ,  $Zn(II)$ ,  $Cu(II)$  and  $Cd(II)$  from aqueous solutions by adsorption onto olive branches activated carbon: Equilibrium and thermodynamic studies. *Chemistry International*, 6(1), 11–20.
- Al-Senani, G. M., & Al-Fawzan, F. F. (2018). Adsorption study of heavy metal ions from aqueous solution by nanoparticle of wild herbs. *Egyptian Journal of Aquatic Research*, 44(3), 187–194. <https://doi.org/10.1016/j.ejar.2018.07.006>
- Arni, S. Al. (2018). Extraction and isolation methods for lignin separation from sugarcane bagasse: A review. In *Industrial Crops and Products* (Vol. 115, pp. 330–339). Elsevier B.V. <https://doi.org/10.1016/j.indcrop.2018.02.012>
- Asasian Kolor, N., Sharifian, S., & Kaghazchi, T. (2019). Investigation of sulfuric acid-treated activated carbon properties. *Turkish Journal of Chemistry*, 43(2), 663–675. <https://doi.org/10.3906/kim-1810-63>
- Azmi, N. B., Bashir, M. J. K., Sethupathi, S., & Ng, C.-A. (2014). Recent Development in Landfill Leachate Treatment Using Low-Cost Adsorbent Prepared From Waste Material. In H. A. Aziz & A. Mojiri (Eds.), *Wastewater Engineering: Advanced Wastewater Treatment Systems* (pp. 6–14). IJSR Publications. <http://www.ijsrpub.com/books>
- Bakar, N. A., Othman, N., Yunus, Z. M., Altowayti, W. A. H., Tahir, M., Fitriani, N., & Mohd-Salleh, S. N. A. (2021). An insight review of lignocellulosic



- materials as activated carbon precursor for textile wastewater treatment. In *Environmental Technology and Innovation* (Vol. 22). Elsevier B.V. <https://doi.org/10.1016/j.eti.2021.101445>
- Bohli, T., Fiol, N., Villaescusa, I., & Ouederni, A. (2013). Adsorption on Activated Carbon from Olive Stones: Kinetics and Equilibrium of Phenol Removal from Aqueous Solution. *Journal of Chemical Engineering & Process Technology*, 04(06), 1-5.
- Bohli, T., Ouederni, A., Fiol, N., & Villaescusa, I. (2015). Evaluation of an activated carbon from olive stones used as an adsorbent for heavy metal removal from aqueous phases. *Comptes Rendus Chimie*, 18(1), 88-99.
- Bu, Q., Lei, H., Wang, L., Yadavalli, G., Wei, Y., Zhang, X., Zhu, L., & Liu, Y. (2015). Biofuel production from catalytic microwave pyrolysis of Douglas fir pellets over ferrum-modified activated carbon catalyst. *Journal of Analytical and Applied Pyrolysis*, 112, 74-79.
- Burakov, A. E., Galunin, E. V., Burakova, I. V., Kucherova, A. E., Agarwal, S., Tkachev, A. G., & Gupta, V. K. (2018). Adsorption of heavy metals on conventional and nanostructured materials for wastewater treatment purposes: A review. In *Ecotoxicology and Environmental Safety* (Vol. 148, pp. 702-712). Academic Press. <https://doi.org/10.1016/j.ecoenv.2017.11.034>
- Carmona, V. B., Oliveira, R. M., Silva, W. T. L., Mattoso, L. H. C., & Marconcini, J. M. (2013). Nanosilica from rice husk: Extraction and characterization. *Industrial Crops and Products*, 43(1), 291-296.
- Dutta, S., Bhaumik, A., & Wu, K. C. W. (2014). Hierarchically porous carbon derived from polymers and biomass: Effect of interconnected pores on energy applications. In *Energy and Environmental Science* (Vol. 7, Issue 11, pp. 3574-3592). Royal Society of Chemistry. <https://doi.org/10.1039/c4ee01075b>
- Elavarasan, R. M. (2018). The Motivation for Renewable Energy and its Comparison with Other Energy Sources: A Review. *European Journal of Sustainable Development Research*, 3(1). <https://doi.org/10.20897/ejosdr/4005>
- Escudero-Oñate, C., Fiol, N., Poch, J., & Villaescusa, I. (2017). Valorisation of Lignocellulosic Biomass Wastes for the Removal of Metal Ions from Aqueous Streams: A Review. In J. S. Tumuluru (Ed.), *Biomass Volume Estimation and Valorization for Energy* (1st ed., pp. 381-407). InTech.
- Fakayode, O. A., Akpabli-Tsigbe, N. D. K., Wahia, H., Tu, S., Ren, M., Zhou, C., & Ma, H. (2021). Integrated bioprocess for bio-ethanol production from watermelon rind biomass: Ultrasound-assisted deep eutectic solvent pretreatment, enzymatic hydrolysis and fermentation. *Renewable Energy*, 180, 258-270.
- Gunawan, S., Hasan, H., & Lubis, R. D. W. (2020). Pemanfaatan Adsorben dari Tongkol Jagung sebagai Karbon Aktif untuk Mengurangi Emisi Gas Buang Kendaraan Bermotor. *Jurnal Rekayasa Material, Manufaktur Dan Energi*, 3(1), 38-47.
- Gupta, H., & Gogate, P. R. (2016). Intensified removal of copper from waste water using activated watermelon based biosorbent in the presence of ultrasound. *Ultrasonics Sonochemistry*, 30, 113-122.
- Holliday, M. C., Parsons, D. R., & Zein, S. H. (2022). Agricultural Pea Waste as a Low-Cost Pollutant Biosorbent for Methylene Blue Removal: Adsorption Kinetics, Isotherm And Thermodynamic Studies. *Biomass Conversion and Biorefinery*. <https://doi.org/10.1007/s13399-022-02865-8>
- Jiang, C., Yakaboylu, G. A., Yumak, T., Zondlo, J. W., Sabolsky, E. M., & Wang, J. (2020). Activated carbons prepared by indirect and direct CO<sub>2</sub> activation of lignocellulosic biomass for supercapacitor electrodes. *Renewable Energy*, 155, 38-52.
- Karaboyaci, M., Tama, B., Şencan, A., & Kiliç, M. (2017). Recycling of Rose Wastes to Activated Carbon with Ecological Precursor. *Bilge International Journal of Science and Technology Research*, 1(1), 1-8.
- Kayranli, B., Gok, O., Gok, G., Celebi, H., Yilmaz, T., Seckin, I. Y., & Kalat, D. (2021). Zinc removal mechanisms with recycled lignocellulose: from fruit residual to biosorbent then soil conditioner. *Water, Air, & Soil Pollution*, 232(311), 1-15.
- Khatoon, H., & Rai, P. N. (2016). Agricultural Waste Materials As Biosorbents For The Removal Of Heavy Metals And Synthetic Dyes-A Review. *Octa Journal of Environmental Research*, 4(3), 208-229. <https://www.researchgate.net/publication/327051571>
- Komkiene, J., & Baltreinaite, E. (2016). Biochar as adsorbent for removal of heavy metal ions [Cadmium(II), Copper(II), Lead(II), Zinc(II)] from aqueous phase. *International Journal of Environmental Science and Technology Volume*, 13, 471-482.
- Kumar, A., & Jena, H. M. (2017). Adsorption of Cr(VI) from aqueous solution by prepared high surface area activated carbon from Fox nutshell by chemical activation with H<sub>3</sub>PO<sub>4</sub>. In *Journal of Environmental Chemical Engineering* (Vol. 5, Issue 2, pp. 2032-2041). Elsevier Ltd. <https://doi.org/10.1016/j.jece.2017.03.035>
- Lakshmana Naik, R., Rupas Kumar, M., & Bala Narsaiah, T. (2023). Removal of heavy metals (Cu & Ni) from wastewater using rice husk and orange peel as adsorbents. *Materials Today: Proceedings*, 72, 92-98.
- Li, H., Xiong, J., Xiao, T., Long, J., Wang, Q., Li, K., Liu, X., Zhang, G., & Zhang, H. (2019). Biochar derived from watermelon rinds as regenerable

- adsorbent for efficient removal of thallium(I) from wastewater. *Process Safety and Environmental Protection*, 127, 257–266. <https://doi.org/10.1016/j.psep.2019.04.031>
- Li, T., & Takkellapati, S. (2018). The current and emerging sources of technical lignins and their applications. *Biofuels, Bioproducts and Biorefining*, 12(5), 756–787.
- Long, H., Li, X., Wang, H., & Jia, J. (2013). Biomass resources and their bioenergy potential estimation: A review. In *Renewable and Sustainable Energy Reviews* (Vol. 26, pp. 344–352). Elsevier Ltd.
- Lu, X., Jiang, J., Sun, K., & Xie, X. (2014). Preparation and characterization of sisal fiber-based activated carbon by chemical activation with zinc chloride. *Bulletin of the Korean Chemical Society*, 35(1), 103–110.
- Malik, R., Lata, S., & Singhal, S. (2015). Removal of heavy metal from wastewater by the use of modified aloe vera leaf powder. *International Journal of Basic and Applied Chemical Sciences*, 5(2), 6–17. <http://www.cibtech.org/jcs.htm>
- Ma'Ruf, A., Pramudono, B., & Aryanti, N. (2017). Lignin isolation process from rice husk by alkaline hydrogen peroxide: Lignin and silica extracted. *AIP Conference Proceedings*, 1823. <https://doi.org/10.1063/1.4978086>
- Mittal, J., Ahmad, R., Mariyam, A., Gupta, V. K., & Mittal, A. (2021). Expeditious and enhanced sequestration of heavy metal ions from aqueous environment by papaya peel carbon: A green and low-cost adsorbent. *Desalination and Water Treatment*, 210, 365–376.
- Mohamed, H. S., Soliman, N. K., Abdelrheem, D. A., Ramadan, A. A., Elghandour, A. H., Ahmed, S. A., & Adsorption, S. A. A. (2019). Adsorption of Cd 2D and Cr 3D ions from aqueous solutions by using residue of Padina gymnospora waste as promising low-cost adsorbent. *Heliyon*, 5, 1287.
- Mustapha, S., Ndamitso, M. M., Abdulkareem, A. S., Tijani, J. O., Mohammed, A. K., & Shuaib, D. T. (2019). Potential of using kaolin as a natural adsorbent for the removal of pollutants from tannery wastewater. *Heliyon*, 5(11). <https://doi.org/10.1016/j.heliyon.2019.e02923>
- Muthusamy, P., & Murugan, S. (2016). Removal of Lead Ion Using Maize Cob as a Bioadsorbent. In *Journal of Engineering Research and Application* [www.ijera.com](http://www.ijera.com) (Vol. 6).
- Obregón-Valencia, D., & Sun-Kou, M. D. R. (2014). Comparative cadmium adsorption study on activated carbon prepared from aguaje (*Mauritia flexuosa*) and olive fruit stones (*Olea europaea* L.). *Journal of Environmental Chemical Engineering*, 2(4), 2280–2288.
- Osman, A. I., Blewitt, J., Abu-Dahrieh, J. K., Farrell, C., Al-Muhtaseb, A. H., Harrison, J., & Rooney, D. W. (2019). Production and characterisation of activated carbon and carbon nanotubes from potato peel waste and their application in heavy metal removal. *Environmental Science and Pollution Research*, 26(36), 37228–37241. <https://doi.org/10.1007/s11356-019-06594-w>
- Özsin, G., Kılıç, M., Apaydın-Varol, E., & Pütün, A. E. (2019). Chemically activated carbon production from agricultural waste of chickpea and its application for heavy metal adsorption: equilibrium, kinetic, and thermodynamic studies. *Applied Water Science*, 9(3). <https://doi.org/10.1007/s13201-019-0942-8>
- Pallarés, J., González-Cencerrado, A., & Arauzo, I. (2018). Production and characterization of activated carbon from barley straw by physical activation with carbon dioxide and steam. *Biomass and Bioenergy*, 115, 64–73. <https://doi.org/10.1016/j.biombioe.2018.04.015>
- Peláez-Cid, A. A., Romero-Hernández, V., Herrera-González, A. M., Bautista-Hernández, A., & Coreño-Alonso, O. (2020). Synthesis of activated carbons from black sapote seeds, characterization and application in the elimination of heavy metals and textile dyes. *Chinese Journal of Chemical Engineering*, 28(2), 613–623. <https://doi.org/10.1016/j.cjche.2019.04.021>
- Pournima, R. P., & Shrikant, M. B. (2018). Experimental dose optimization for Cu removal from water using neem leaves. *Int J Curr Eng Technol*, 8(5), 1329–1332.
- Rápó, E., & Tonk, S. (2021). Factors affecting synthetic dye adsorption; desorption studies: A review of results from the last five years (2017–2021). In *Molecules* (Vol. 26, Issue 17). MDPI.
- Razi, M. A. M., Al-Gheethi, A., & Za, A. (2018). Removal of Heavy Metals from Textile Wastewater Using Sugarcane Bagasse Activated Carbon. *International Journal of Engineering & Technology*, 7(4), 112–115.
- Saleem, J., Shahid, B. U., Hijab, M., Mackey, H., & McKay, G. (2019). Production and applications of activated carbons as adsorbents from olive stones. *Biomass Conversion and Biorefinery*, 775–802.
- Salih, A. M., Williams, C., & Khanaqa, P. (2021). Kinetic Studies of Heavy Metal Removal from Industrial Wastewater by Using Natural Zeolite. *UKH Journal of Science and Engineering*, 5.
- Shafiq, M., Alazba, A. A., & Amin, M. T. (2018). Removal of heavy metals from wastewater using date palm as a biosorbent: A comparative review. In *Sains Malaysiana*. 47 (1): 35–49.
- Soliman, N. K., & Moustafa, A. F. (2020). Industrial solid waste for heavy metals adsorption features and challenges; a review. *Journal of Materials Research and Technology*, 9(5), 10235–10253.
- Šoštarić, T. D., Petrović, M. S., Pastor, F. T., Lončarević, D. R., Petrović, J. T., Milojković, J. V., & Stojanović, M. D. (2018). Study of heavy metals biosorption on native and alkali-treated apricot shells and its

- application in wastewater treatment. *Journal of Molecular Liquids*, 259, 340-349. <https://doi.org/10.1016/j.molliq.2018.03.055>
- Thotagamuge, R., Kooh, M. R. R., Mahadi, A. H., Lim, C. M., Abu, M., Jan, A., Hanipah, A. H. A., Khiong, Y. Y., & Shofry, A. (2021). Copper modified activated bamboo charcoal to enhance adsorption of heavy metals from industrial wastewater. *Environmental Nanotechnology, Monitoring and Management*, 16. <https://doi.org/10.1016/j.enmm.2021.100562>
- Vukelic, D., Boskovic, N., Agarski, B., Radonic, J., Budak, I., Pap, S., & Turk Sekulic, M. (2018). Eco-design of a low-cost adsorbent produced from waste cherry kernels. *Journal of Cleaner Production*, 174, 1620-1628. <https://doi.org/10.1016/j.jclepro.2017.11.098>
- Vunain, E., Njewa, J. B., Biswick, T. T., & Ipadeola, A. K. (2021). Adsorption of chromium ions from tannery effluents onto activated carbon prepared from rice husk and potato peel by H3PO4 activation. *Applied Water Science*, 11(9). <https://doi.org/10.1007/s13201-021-01477-3>
- Yahya, M. A., Al-Qodah, Z., & Ngah, C. W. Z. (2015). Agricultural bio-waste materials as potential sustainable precursors used for activated carbon production: A review. In *Renewable and Sustainable Energy Reviews* (Vol. 46, pp. 218-235). Elsevier Ltd. <https://doi.org/10.1016/j.rser.2015.02.051>
- Yeow, P. K., Wong, S. W., & Hadibarata, T. (2021). Removal of azo and anthraquinone dye by plant biomass as adsorbent - a review. In *Biointerface Research in Applied Chemistry* (Vol. 11, Issue 1, pp. 8218-8232). AMG Transcend Association.
- Zhou, Q., Yang, N., Li, Y., Ren, B., Ding, X., Bian, H., & Yao, X. (2020). Total concentrations and sources of heavy metal pollution in global river and lake water bodies from 1972 to 2017. *Global Ecology and Conservation*, 22.
- Zhu, S., Sun, H., Mu, T., Li, Q., & Richel, A. (2023). Preparation of cellulose nanocrystals from purple sweet potato peels by ultrasound-assisted maleic acid hydrolysis. *Food Chemistry*, 403.

# The Potential of Biomass-Based Activated Carbon to Remove Heavy Metals in Wastewater – A Review

## ORIGINALITY REPORT

16%

SIMILARITY INDEX

11%

INTERNET SOURCES

11%

PUBLICATIONS

1%

STUDENT PAPERS

## PRIMARY SOURCES

1	<a href="http://www.researchgate.net">www.researchgate.net</a> Internet Source	2%
2	<a href="http://link.springer.com">link.springer.com</a> Internet Source	1%
3	"Textile Wastewater Treatment", Springer Science and Business Media LLC, 2022 Publication	1%
4	Norshila Abu Bakar, Norzila Othman, Zalilah Murni Yunus, Wahid Ali Hamood Altowayti et al. "An insight review of lignocellulosic materials as activated carbon precursor for textile wastewater treatment", Environmental Technology & Innovation, 2021 Publication	1%
5	<a href="http://jurnal.untad.ac.id">jurnal.untad.ac.id</a> Internet Source	1%
6	<a href="http://discol.umk.edu.my">discol.umk.edu.my</a> Internet Source	<1%
7	<a href="http://digiresearch.vut.ac.za">digiresearch.vut.ac.za</a>	

---

Internet Source

<1 %

---

8

[tesisred.net](https://tesisred.net)

Internet Source

<1 %

---

9

[www2.mdpi.com](https://www2.mdpi.com)

Internet Source

<1 %

---

10

Femina Carolin C, T. Kamalesh, P. Senthil Kumar, Gayathri Rangasamy. "A Critical Review on the Sustainable Approaches for the Removal of Toxic Heavy Metals from Water Systems", Industrial & Engineering Chemistry Research, 2023

Publication

<1 %

---

11

Pranoto Pranoto, Venty Suryanti, Robi'atul Adawiyah. "Andisol and microcrystalline cellulose from Typha angustifolia for auramine O adsorption", International Journal of Advances in Applied Sciences, 2023

Publication

<1 %

---

12

[utpedia.utp.edu.my](https://utpedia.utp.edu.my)

Internet Source

<1 %

---

13

Paola Santander, Bryan Butter, Estefanía Oyarce, Mauricio Yáñez, Ling-Ping Xiao, Julio Sánchez. "Lignin-based adsorbent materials for metal ion removal from wastewater: A review", Industrial Crops and Products, 2021

Publication

<1 %

---

14 "Green Technologies for Sustainable Water Management", American Society of Civil Engineers (ASCE), 2016 <1 %  
Publication

---

15 Norfahana Abd-Talib, Chuo Sing Chuong, Siti Hamidah Mohd-Setapar, Umi Asiah Asli, Khairul Faizal Pa'ee, Kelly Yong Tau Len. "Trends in Adsorption Mechanisms of Fruit Peel Adsorbents to Remove Wastewater Pollutants (Cu (II), Cd (II) and Pb (II))", Journal of Water and Environment Technology, 2020 <1 %  
Publication

---

16 [assets.researchsquare.com](https://assets.researchsquare.com) <1 %  
Internet Source

---

17 [prp.hec.gov.pk](https://prp.hec.gov.pk) <1 %  
Internet Source

---

18 [aran.library.nuigalway.ie](https://aran.library.nuigalway.ie) <1 %  
Internet Source

---

19 [researchrepository.wvu.edu](https://researchrepository.wvu.edu) <1 %  
Internet Source

---

20 [www.siftdesk.org](https://www.siftdesk.org) <1 %  
Internet Source

---

21 "Handbook of Environmental Materials Management", Springer Science and Business Media LLC, 2019 <1 %  
Publication

---

22	"Pollutants and Water Management", Wiley, 2021 Publication	<1 %
23	Tatiana Aurora Condezo Castro, Marcelo Cardoso, Ana Augusta Passos Rezende, Angélica de Cássia Oliveira Carneiro et al. "Possible alternatives for using kraft lignin as activated carbon in pulp mills– a review", Nordic Pulp & Paper Research Journal, 2023 Publication	<1 %
24	<a href="http://acris.aalto.fi">acris.aalto.fi</a> Internet Source	<1 %
25	<a href="http://atrium.lib.uoguelph.ca">atrium.lib.uoguelph.ca</a> Internet Source	<1 %
26	<a href="http://bioresources.cnr.ncsu.edu">bioresources.cnr.ncsu.edu</a> Internet Source	<1 %
27	<a href="http://eprints.uthm.edu.my">eprints.uthm.edu.my</a> Internet Source	<1 %
28	<a href="http://helda.helsinki.fi">helda.helsinki.fi</a> Internet Source	<1 %
29	<a href="http://iwaponline.com">iwaponline.com</a> Internet Source	<1 %
30	<a href="http://pure.sruc.ac.uk">pure.sruc.ac.uk</a> Internet Source	<1 %
31	<a href="http://www.frontiersin.org">www.frontiersin.org</a> Internet Source	<1 %

<1 %

32

[www.ijert.org](http://www.ijert.org)

Internet Source

<1 %

33

Abdullah, M.O.. "Automobile adsorption air-conditioning system using oil palm biomass-based activated carbon: A review", Renewable and Sustainable Energy Reviews, 201105

Publication

<1 %

34

Ekta R. Raut, Monita A. Bedmohata Thakur, Archana R. Chaudhari. "A review on activated carbon preparation from natural and eco-friendly raw materials", AIP Publishing, 2021

Publication

<1 %

35

Rafael M. Dias, Lívia C. G. Petrin, Filipe H. B. Sosa, André M. da Costa Lopes, João A. P. Coutinho, Mariana C. da Costa. "Investigation of Kraft Lignin Solubility in Protic Ionic Liquids and Their Aqueous Solutions", Industrial & Engineering Chemistry Research, 2020

Publication

<1 %

36

Risha Jasmine Singh, Candace E. Martin, Dave Barr, Rhonda J. Rosengren. "Cucumber peel bead biosorbent for multi-ion decontamination of drinking water collected from a mine region in New Zealand", Environmental Technology, 2019

Publication

<1 %



---

37 Shuang Wang, Hoseok Nam, Doyeon Lee, Hyungseok Nam. "H<sub>2</sub>S gas adsorption study using copper impregnated on KOH activated carbon from coffee residue for indoor air purification", Journal of Environmental Chemical Engineering, 2022

Publication

<1 %

---

38 Yasmin Vieira, Juliana M.N. dos Santos, Jordana Georjina, Marcos L.S. Oliveira, Diana Pinto, Guilherme L. Dotto. "An overview of forest residues as promising low-cost adsorbents", Gondwana Research, 2022

Publication

<1 %

---

39 [digi.lib.ttu.ee](http://digi.lib.ttu.ee)

Internet Source

<1 %

---

40 [ir.mu.ac.ke:8080](http://ir.mu.ac.ke:8080)

Internet Source

<1 %

---

41 [ouci.dntb.gov.ua](http://ouci.dntb.gov.ua)

Internet Source

<1 %

---

42 [ourarchive.otago.ac.nz](http://ourarchive.otago.ac.nz)

Internet Source

<1 %

---

43 [psasir.upm.edu.my](http://psasir.upm.edu.my)

Internet Source

<1 %

---

44 [qu.edu.iq](http://qu.edu.iq)

Internet Source

<1 %

---

- |    |   |      |
|----|---|------|
| 45 | <a href="https://repository.unhas.ac.id">repository.unhas.ac.id</a><br>Internet Source  | <1 % |
| 46 | <a href="https://sutir.sut.ac.th:8080">sutir.sut.ac.th:8080</a><br>Internet Source  | <1 % |
| 47 | <a href="http://www.ajol.info">www.ajol.info</a><br>Internet Source   | <1 % |
| 48 | "Green Adsorbents to Remove Metals, Dyes and Boron from Polluted Water", Springer Science and Business Media LLC, 2021<br>Publication   | <1 % |
| 49 | Renu, Madhu Agarwal, K. Singh. "Heavy metal removal from wastewater using various adsorbents: a review", Journal of Water Reuse and Desalination, 2017<br>Publication                                     | <1 % |
| 50 | Tadele Assefa Aragaw, Fekadu Mazengiaw Bogale. "Biomass-Based Adsorbents for Removal of Dyes From Wastewater: A Review", Frontiers in Environmental Science, 2021<br>Publication                          | <1 % |
| 51 | Diego Ramón Lobato-Peralta, Estefanía Duque-Brito, Heidi Isabel Villafán Vidales, Adriana Longoria et al. "A review on trends in lignin extraction and valorization of lignocellulosic biomass for energy | <1 % |

52

S. Pavithra, Thandapani Gomathi, S. Sugashini, P.N. Sudha, Hussein H. Alkhamis, Abdulwahed F. Alrefaei, Mikhlid H. Almutairi. "Batch adsorption studies on surface tailored chitosan/orange peel hydrogel composite for the removal of Cr(VI) and Cu(II) ions from synthetic wastewater", Chemosphere, 2021

<1 %

Publication

---

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

# The Potential of Biomass-Based Activated Carbon to Remove Heavy Metals in Wastewater – A Review

---

GRADEMARK REPORT

---

FINAL GRADE

**/0**

GENERAL COMMENTS

**Instructor**

---

PAGE 1

---

PAGE 2

---

PAGE 3

---

PAGE 4

---

PAGE 5

---

PAGE 6

---

PAGE 7

---

PAGE 8

---

PAGE 9

---

PAGE 10

---