

## Encapsulation of Alkaline Phosphatase in Mesoporous Methyl-Silica Hybrid by Sol-Gel Process

Sriyanti <sup>a\*</sup>

a Inorganic Chemistry Laboratory, Chemistry Department, Faculty of Sciences and Mathematics, Diponegoro University, Jalan Prof. Soedarto, Tembalang, Semarang 50275

\* Corresponding author: [sriyanti@live.undip.ac.id](mailto:sriyanti@live.undip.ac.id)

### Article Info

Keywords:  
 encapsulation,  
 alkaline  
 phosphatase,  
 methyl-silica  
 hybrid, sol-gel

### Abstract

In recent years, the sol-gel technique has attracted increasing interest as a unique approach to immobilize biomolecules for bioanalytical applications as well as biochemical and biophysical studies. In this research, encapsulation of Alkaline Phosphatase (ALP) enzyme in mesoporous methyl-silica hybrid by sol-gel process has been carried out. Mesoporous methyl-silica hybrid has been synthesis by using tetraethylorthosilicate (TEOS) and methyltriethoxysilane (MTES) as precursor and poly(ethylene) glycol (PEG) as a polymer dopant. The preparation of methyl-silica hybrid was carried out at various mol ratios of precursors and PEG concentration. Encapsulation was emphasized by mixing sol solution and tris-HCl buffer containing ALP. The Surface Area Analyzer analysis data showed that the pore diameter and surface area of methyl-silica hybrid tended to increase as the PEG dopant concentration increases. Result showed that ALP encapsulated in the methyl-silica hybrids with PEG dopant gave enzymatic activity as 0.112 U/mg enzyme, higher than ALP encapsulated in copolymerization of TEOS with MTES or in silica from TEOS precursor only (0.098 U/mg enzyme and 0.069 U/mg enzyme, respectively). It was shown that copolymerization of TEOS with organosilane precursor and the entrapment of polymer additives into sol-gel processed materials are useful methods for modifying the internal environment and hence the activity of biomolecules entrapped in sol-gel derived biomaterials.

### 1. Introduction

Encapsulation of biomolecules such as enzymes, proteins, cells and microorganisms in porous metal oxides by physical entrapment via sol-gel process has drawn great interest in recent years. The encapsulation of enzymes by sol-gel methods is commonly carried out through four stages, namely acid catalyzed hydrolysis of alkoxysilane precursors, addition of aqueous buffer solution containing enzyme, aging and drying to produce optically transparent glass materials with the enzyme entrapped [1-3].

The entrapment of protein into a silica matrix can result in a range of possible environments for the entrapped protein. Some of the proteins are entrapped in pores which are completely accessible to the analyte, some in the pores that are partially accessible, while the remainder of the protein may be sequestered into pores which are completely inaccessible. Pore sizes of the silica

matrices and analyte-matrix interactions such as electrostatic, hydrogen bonding and hydrophobic interactions play an important role in determining the accessibility of an analyte to entrapped proteins [4, 5]. Therefore, in order to maximize the accessibility, some modifications should be employed including manipulation of sol-gel synthesis conditions, incorporation of polymer or other additives, manipulation of aging conditions to minimize silanol content, manipulation of pH conditions or use of templating agents to promote larger pores (mesopores) [6].

In this research, encapsulation of Alkaline Phosphatase (ALP) enzyme in mesoporous methyl-silica hybrid by sol-gel process has been carried out. Mesoporous methyl-silica hybrid has been synthesis by using tetraethylorthosilicate (TEOS) and methyltriethoxysilane (MTES) as precursor and poly(ethylene) glycol (PEG) as a polymer dopant.

## 2. Experimental

**Material and Methods:** Alkaline phosphatase (ALP) (EC 3.1.3.1, type I-S, from bovine intestinal mucosa), bovine serum albumin (BSA), p-nitrophenyl phosphate, tris-HCl buffer, glycine buffer were supplied by Sigma. Tetraethylorthosilicate (TEOS), Methyl triethoxysilane (MTES) and polyethylene glycol (PEG, MW 600) were purchased from Sigma.

The preparation of alkaline phosphatase, ALP, immobilized silica sol-gel materials followed procedures of Avnir *dkk.* [2], Keeling-Tucker *dkk.* [6], and Wei *dkk.* [5], with some modification.

### Preparation of polymer template containing silica sol-gel material.

In this work, PEG 600 and PVA 13,000-23,000 used as templates. Typically, TEOS was prehydrolyzed with water in ethanol using HCl as catalyst at [TEOS]:[H<sub>2</sub>O]:[EtOH]:[HCl] molar ratio of 1:4:3:0.0005 under magnetic stirring at room temperature. After 30 minutes, the precursors mixture became homogenous. The hydrolyzed solution was stored for 3 days in a freezer before use to ensure complete hydrolysis. Furthermore, the prehydrolyzed solution was added to a specific amount of aqueous template solution ranging from 10 to 40 wt%. The resultant homogenous sol was sealed with paraffin film containing several pinholes to allow for slow evaporation of solvents and reaction by products at room temperature.

To prepare the mesoporous silica material, the sample was ground and extracted with water to remove the template from the synthesized silica materials at room temperature. A certain amount of sample (e.g. 0.2-1.0 g depending on the template content) was ground into powder, which was soaked in 15 mL water under stirring for 30 minutes. After centrifugation and decantation, the sample was placed in another 15 mL of fresh water for 3 h. The mixture was again centrifuged and soaked in 15 mL water overnight. In the following two days, the sample was washed twice a day in the same manner. After extraction, the sample was dried at room temperature.

### Immobilisation of alkaline phosphatase in silica sol-gel material.

The ALP was added to the prehydrolyzed precursor before gelation. In a typical procedure for the preparation of enzyme-doped silica sol-gel: TEOS (2mL) was mixed with H<sub>2</sub>O (0.48 mL) and HCl (0.015N, 16μL) in a flask under sonication at room temperature for 30 minutes. A volume of 1.5 mL hydrolyzed TEOS was then mixed with 2.5 mL of a tris-HCl buffer (40 mM, pH 8.5) containing ALP (a tris-HCl buffer solution containing ALP prepared by dissolving 2 mg of the ALP in tris-HCl buffer solution 40 mM, pH 8.5) and between 0 and 20 weight % of PEG or PVA solution. The mixture was placed in a flask that was then sealed with paraffin film and allowed to gel at room temperature. Upon gelation, several small holes were punched in the paraffin film to allow the evaporation to solvents and put into vacuum dessicator and continually evacuated for 10 days at room temperature until constant weight was reached.

### Detection Method:

Fourier transform infrared (FTIR) spectroscopy was used to characterize the presence of specific chemical groups in the materials and to monitor the template removal. The as-synthesized and water extracted samples were milled and mixed with dried KBr powder. FTIR spectra were obtained within the range 4000 and 400 cm<sup>-1</sup>.

### Activity assay for free and entrapped enzyme.

General procedure for enzymatic activity assays of ALP in solution and in immobilized form were adapted from the literatures. Kinetic parameters for the free and immobilized enzymes were determined using Michaelis-Menten kinetic [5].

The initial activity of ALP was determined from the absorbance change at 405 nm by using a UV-Vis spectrometer. The absorbance increase was due to the formation of p-nitrophenol. For free ALP, 1 mL of the enzyme solution (containing 2μg ALP) was mixed with 1.46 ml of tris-HCl buffer and 0.3 mL of MgCl<sub>2</sub> 0.01M. After 30 minutes, 0.24 mL of p-nitrophenyl phosphate 0.1 M was added to initiate reaction, upon which the absorbance change with time was recorded. For immobilized ALP, all samples were first washed with dilute buffer solution before proceeding with the activity assay according to the following procedure. The sample (containing 0.08 units of ALP) was weight into a tube and 10 mL tris-HCl buffer was added to soak the sample under agitation. After 1 h, the washed solution was separated from the solid by decantation after centrifugation. The washing procedure was repeated two more times at 1 h intervals. The ALP containing gel was then evaluated for the apparent activity following the same procedure as for the free ALP except substituting the enzyme solution with 1 mL of H<sub>2</sub>O. The sample was weighed into the assay mixture consisting of 1 mM of MgCl<sub>2</sub> and 40 mM of tris-HCl buffer pH 8.5. The assays were performed at room temperature.

The kinetic parameters were determined by varying the concentration of substrate, p-nitrophenyl phosphate (p-NPP), from 1 to 15 mM. The effect of pH on the catalytic activity of ALP in free and encapsulated form was evaluated by measuring initial velocity of the reaction in buffers at different pH using fixed concentration of p-NPP (8mM). The buffers used were 40mM tris-HCl buffers at pH values 7 to 8.5 at 0.5 intervals and glycine buffer for pH values 9 to 10.

## 3. Results and Discussion

The preparation of enzyme containing sol-gel materials was performed by adding the enzymes with PEG as template, into The hybrids TEOS-MTES derived sol before gelation, followed by aging and drying the gel to yield the transparent enzyme-containing glasses. The gelation time was shortened by the addition of the buffered enzyme solution which raised the pH of the mixture. The aging and drying process were accelerated by using a vacuum dessicator to evacuate solvents and by-product of the sol-gel reaction without causing



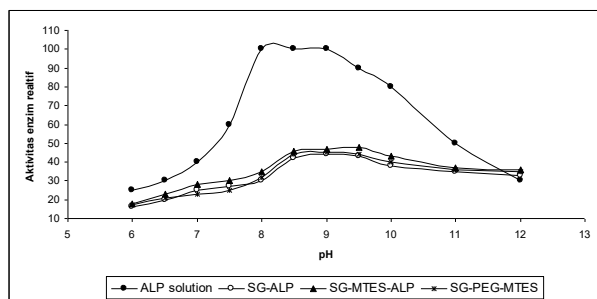


Figure 2. Influence of pH for enzymatic activity of ALP in silica-PEG and Silica-MTES.

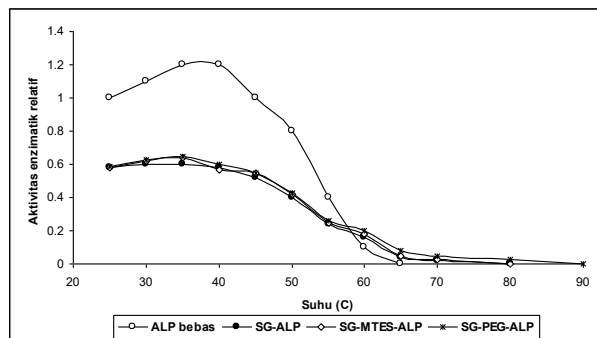


Figure 3. influence of temperature.

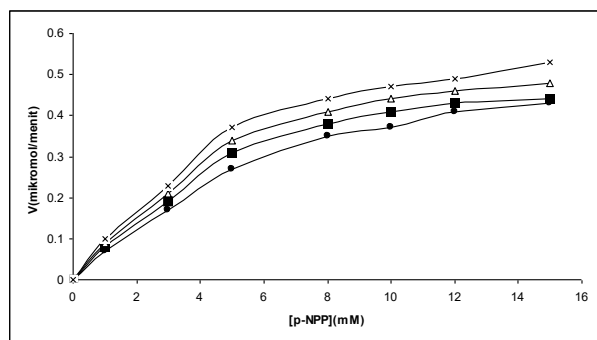


Figure 4. Michaelis-Menten curve for entrapped alkaline phosphatase in : (●) SG-ALP, (■) SG-5%PEG, (◇) SG-10%PEG dan (x) SG-20%PEG.

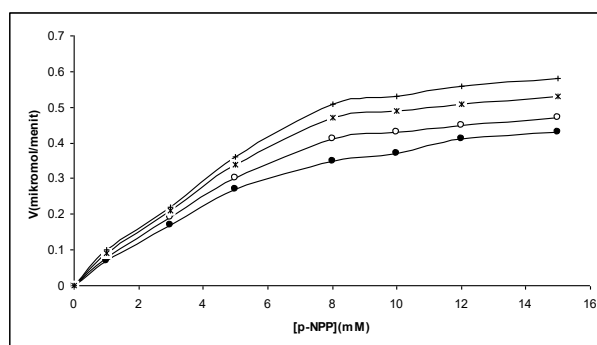


Figure 5. Michaelis-Menten curve from entrapped alkaline phosphatase in: (●) SG-ALP, (○) SG-10%MTES, (\*) SG-20%MTES dan (+) SG-40%MTES.

Table 2. enzymatic activity datas.

No.	ALP enzyme in:	Km (mM)	Vmax (μM/minute)	Spesific actv. (μmol menit <sup>-1</sup> / mg enzim)
1.	Solution	0,077	6,988	3,494
2.	SG	9,563	0,738	0,069
3.	SG-5%MTES	8,366	0,749	0,090
	SG-10% MTES	7,618	0,775	0,093
	SG-20% MTES	7,105	0,809	0,098
4.	SG- MTES-5%PEG	9,153	0,810	0,099
	SG-MTES-10%PEG	9,321	0,925	0,103
	SG-MTES-20%PEG	8,552	0,945	0,112

#### 4. Conclusion

Result showed that ALP encapsulated in the ethyl-silica hybrids with PEG dopant gave enzymatic activity as 0.112 U/mg enzyme, higher than ALP encapsulated in copolymerization of TEOS with MTES or in silica from TEOS precursor only (0.098 U/mg enzyme and 0.069 U/mg enzyme, respectively). It was shown that copolymerization of TEOS with organosilane precursor and the entrapment of polymer additives into sol-gel processed materials are usefull methods for modifying the internal environment and hence the activity of biomolecules entrapped in sol-gel derived biomaterials.

#### 5. References

- [1] John D. Brennan, Using Intrinsic Fluorescence to Investigate Proteins Entrapped in Sol-Gel Derived Materials, *Applied Spectroscopy*, 53, 3, (1999) 106A-121A <http://dx.doi.org/10.1366/0003702991946514>
- [2] David Avnir, Sergei Braun, Ovadia Lev, Michael Ottolenghi, Enzymes and Other Proteins Entrapped in Sol-Gel Materials, *Chemistry of Materials*, 6, 10, (1994) 1605-1614 <http://dx.doi.org/10.1021/cm00046a008>
- [3] Bakul C. Dave, Bruce Dunn, Joan Selverstone Valentine, Jeffrey I. Zink, Sol-gel encapsulation methods for biosensors, *Analytical Chemistry*, 66, 22, (1994) 1120A-1127A <http://dx.doi.org/10.1021/ac00094a001>
- [4] Wen Jin, John D. Brennan, Properties and applications of proteins encapsulated within sol-gel derived materials, *Analytica Chimica Acta*, 461, 1, (2002) 1-36 [https://doi.org/10.1016/S0003-2670\(02\)00229-5](https://doi.org/10.1016/S0003-2670(02)00229-5)
- [5] Yen Wei, Jigeng Xu, Qiuwei Feng, Hua Dong, Muduo Lin, Encapsulation of enzymes in mesoporous host materials via the nonsurfactant-templated sol-gel process, *Materials Letters*, 44, 1, (2000) 6-11 [http://dx.doi.org/10.1016/S0167-577X\(99\)00287-6](http://dx.doi.org/10.1016/S0167-577X(99)00287-6)
- [6] Tracey Keeling-Tucker, Michael Rakic, Cassandra Spong, John D. Brennan, Controlling the Material Properties and Biological Activity of Lipase within Sol-Gel Derived Bioglasses via Organosilane and Polymer Doping, *Chemistry of Materials*, 12, 12, (2000) 3695-3704 <http://dx.doi.org/10.1021/cm000491m>