

Original Research Article

Effect of Macroporous Chitosan-Tripolyphosphate Beads on COD and Turbidity Values in Sasirangan Wastewater

Dahlena Ariyani^{1,2}, Riana Maulana², Utami Irawati¹, Dwi Rasy Mujiyanti^{1*}, Dewi Umaningrum¹

¹Departement of Chemistry, Faculty of Mathematics and Natural Science, Universitas Lambung Mangkurat, Jalan A. Yani KM 36, Banjarbaru, Indonesia 70714

²Laboratory of Biomaterial Chemistry, Faculty of Mathematics and Natural Science, Universitas Lambung Mangkurat, Jalan A. Yani KM 36, Banjarbaru, Indonesia 70714

*Corresponding author: drmujiyanti@ulm.ac.id

Copyright © 2026 by Authors,
Published by Environmental Engineering Department,
Faculty of Engineering, Universitas Diponegoro
This open access article is distributed under a
Creative Commons Attribution 4.0 International License



Abstract

A batch system was applied to study the effect of using macroporous cross-linked chitosan-tripolyphosphate (TPP) beads on chemical oxygen demand (COD) values and turbidity in Sasirangan wastewater. The ionic cross-linking reagent, sodium tripolyphosphate, was used to obtain more rigid chitosan beads, and sodium bicarbonate was added as a porogen. COD values were analyzed using the titrimetric method, and turbidity values were analyzed using the turbidimetric method. This analysis was used to study the effect of dose and pH on the performance of beads in Sasirangan wastewater. Scanning electron microscopy (SEM) characterization of the beads showed that NaHCO₃ as a porogen enlarged the pores in the chitosan-TPP beads, and Fourier-transform infrared (FTIR) characterization showed interactions among chitosan, chitosan-TPP beads, and wastewater. The results showed that higher chitosan dosages resulted in increased final COD values in Sasirangan wastewater, and the higher the pH, the higher the COD value. The addition of beads reduced the turbidity value of the Sasirangan wastewater, with higher doses leading to greater turbidity reduction, with the optimum achieved at 400 mL/L. The pH conditions did not affect the reduction in the turbidity value, with less than 1% variation observed.

Keywords: Chemical oxygen demand (COD); hitosan-tripolyphosphate (TPP) beads, sasirangan wastewater; turbidity

1. Introduction

The textile industry is recognized as a major contributor to environmental pollution, particularly due to the discharge of dye-laden effluents into natural water bodies. Even at very low concentrations, textile dyes remain highly visible and can exert toxic effects on aquatic organisms, thereby disrupting ecosystems and deteriorating water quality (Nurmasari et al., 2018; Utami & Nurmasari, 2012). A notable example can be found in South Kalimantan, Indonesia, where the traditional Sasirangan textile industry generates large volumes of wastewater characterized by elevated chemical oxygen demand (COD) and turbidity, two critical indicators of organic pollution (Khair & Noraida, 2025; Nooryaneti et al., 2023). If untreated, this wastewater poses severe risks to aquatic life, destabilizes ecological balance, and limits the usability of water resources. Despite increasing awareness, Sasirangan wastewater treatment remains

challenging because of its complex pollutant composition and the absence of cost-effective, environmentally friendly treatment technologies suitable for small-scale industries. Conventional treatment methods are often inefficient or economically unfeasible for local artisans, highlighting the urgent need for alternative solutions that can effectively reduce COD and turbidity at a low cost.

Several conventional and advanced methods have been applied to treat textile effluents. Coagulation–flocculation is simple and effective for turbidity removal; however, it generates large volumes of sludge and is ineffective in removing soluble dyes (Bratby, 2016; Verma et al., 2012). Oxidation processes (ozone and chlorine) rapidly degrade chromophores; however, they require high chemical inputs and may produce harmful byproducts (Robinson et al., 2001). Fenton’s reagent achieves strong mineralization; however, it is effective only under acidic pH and produces iron sludge (Nidheesh & Gandhimathi, 2012). Advanced oxidation processes (AOPs), such as UV/H₂O₂ and O₃/UV, can completely mineralize dyes; however, their high energy costs and sophisticated setups make them unsuitable for small-scale Sasirangan industries (Oturán & Aaron, 2014). In contrast, adsorption offers a low-cost, eco-friendly, and easy-to-implement option that does not generate hazardous byproducts or large volumes of sludge.

Adsorption has emerged as a promising technique for treating textile effluents because of its simplicity, efficiency, and cost-effectiveness. Among the various adsorbents studied, chitosan has garnered attention for its high adsorption capacity, non-toxicity, biodegradability, and antimicrobial properties (Khubiev et al., 2023; Ravi Kumar, 2000). However, native chitosan has limitations in acidic environments, where it tends to dissolve and lose structural integrity. To overcome this limitation, chemical modification through ionic cross-linking with sodium – TPP has been proposed to enhance chitosan stability and mechanical strength (Crini & Badot, 2008). Native chitosan, despite its high adsorption capacity and biodegradability, suffers from poor stability in acidic environments, where it tends to dissolve and lose structural integrity. To address this limitation, ionic cross-linking with sodium – TPP has been widely applied, as it enhances the chemical stability and mechanical strength of the polymer matrix (Crini & Badot, 2008). However, this modification can also restrict the number of accessible active sites, thereby reducing the overall adsorption efficiency (Nurmasari et al., 2018; Syauqiah et al., 2011; Vakili et al., 2014; Zhao et al., 2016). To mitigate this drawback, recent studies have explored the incorporation of porogens, such as sodium bicarbonate (NaHCO₃), during bead synthesis. The decomposition of NaHCO₃ releases CO₂, generating interconnected macropores within the bead structure. These macropores increase the surface area and diffusion pathways, resulting in markedly enhanced porosity and adsorption performance (Ariyani et al., 2021; Chiou & Li, 2003; Mi et al., 2003; Rockson-Itiveh et al., 2024).

Although previous studies have widely demonstrated the effectiveness of chitosan-based beads in removing dyes from textile wastewater, most evaluations have been limited to color as the primary indicator. However, as shown in Table 1, Sasirangan wastewater is also characterized by the dichromate titrimetric method (276.9 mg/L) and the nephelometric method (676 NTU), both of which surpass national discharge standards and represent critical ecological risks. These parameters, which reflect the organic load and suspended solids, respectively, are more directly relevant to regulatory compliance and environmental sustainability. Despite their importance, limited research has systematically examined the factors, such as pH and adsorbent dosage, that influence the ability of macroporous chitosan–TPP beads to reduce COD and turbidity. Therefore, this study aimed to address this gap and expand the application of chitosan-based adsorbents beyond color removal toward comprehensive wastewater quality improvement.

2. Methods

This study was experimental in nature and was conducted to evaluate the performance of macroporous chitosan–TPP beads in reducing turbidity and chemical oxygen demand (COD) of Sasirangan textile wastewater. Sampling and preliminary testing were performed in the Banjarmasin

region, South Kalimantan, Indonesia (approx. 3.32° S, 114.59° E; $3^{\circ}19'$ S, $114^{\circ}35'$ E). Laboratory-scale synthesis and treatment experiments were conducted at the Chemistry Laboratory, Faculty of Mathematics and Natural Sciences. The samples were stored in clean, closed containers and placed in a dry and dark room to minimize compositional changes. The samples were stored in clean, closed containers, placed in a dry and dark room to minimize changes in composition. Prior to treatment, initial COD and turbidity values were measured using a UV-Vis spectrophotometer and a turbidimeter as baseline references for comparison. The flow chart of the study is shown in Figure 1.

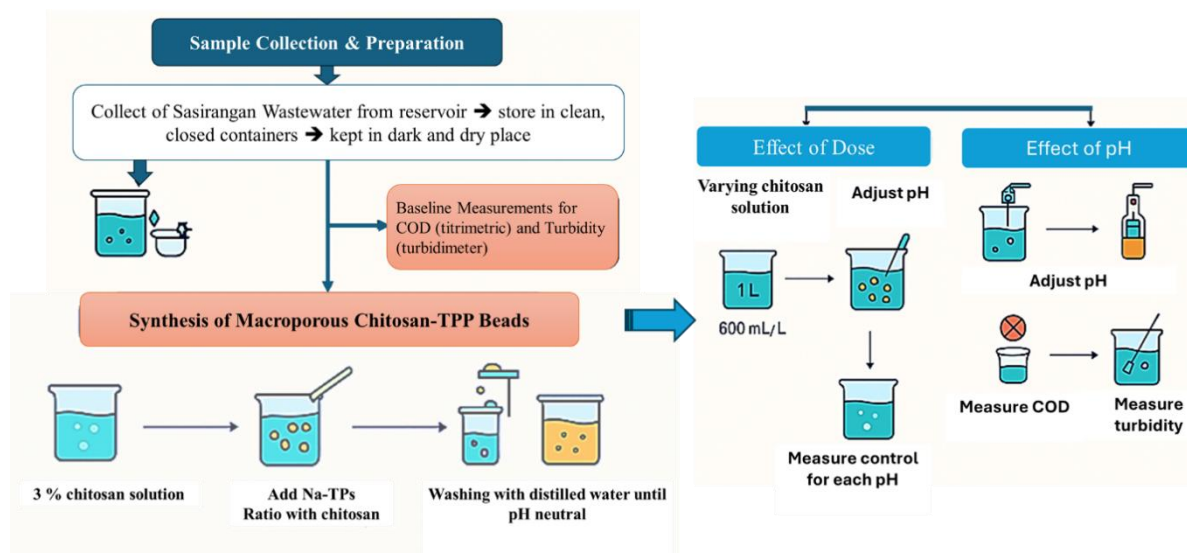


Figure 1. Flow diagram of Sasirangan wastewater treatment process: sample collection, synthesis of chitosan-TPP beads, and adsorption tests

2.1. Effect of Dose on The Ability of Beads in The Treatment of Sasirangan Wastewater

In this study, the chitosan-TPP bead synthesis procedure was based on the method used by Azkia et al. (2021), with several modifications. The chitosan dosage was determined based on the amount of 3% chitosan solution used to make beads for 1 L of sasirangan wastewater, with variations of 300, 400, 500, and 600 mL/L. A dosage of 300 mL/L of 3% chitosan solution was taken as much as 300 mL, and 0.2 g of NaHCO_3 was added and stirred until foamy. To make beads, the chitosan solution was foamed and then soaked in a sodium-TPP solution for 24 hours. A total of 1 L of sasirangan liquid waste solution was prepared and added with 300 mL of chitosan-TPP beads, and the filtrate was then separated by filtering with Whatman No. 42 paper. The resulting filtrate was measured against the COD value and turbidity. The same procedure was carried out for variations in the dosage of chitosan solution at 400, 500, and 600 mL/L. The dosage of 300 mL/L was prepared at a 1:1 ratio of Na-TPP solution to chitosan solution. The negative control was prepared with one beaker containing 500 mL of sasirangan waste without adding beads.

2.2. Effect of pH on the Ability of Beads in the Treatment of Sasirangan Wastewater

The optimum dose of chitosan solution was determined using the procedure described above. It was used to study the effect of wastewater pH on the ability of beads to treat Sasirangan wastewater (the same procedure was performed to determine the effect of the dose). A total volume of 500 mL was used. The initial pH of the waste solution was set to pH 3, then contacted with beads by stirring for 5 min and allowed to stand. The beads and filtrate were separated by filtering with Whatman No. 42 paper. The resulting filtrate was measured for COD and turbidity values. The same procedure was carried out for variations in the initial pH of the wastewater, namely, pH 5, pH 7, and pH 9. A negative control was also

prepared with four beakers containing 500 mL of Sasirangan wastewater without adding beads at settings of pH 3, pH 5, pH 7, and pH 9.

3. Result and Discussion

3.1. Initial Characterization of Sasirangan Wastewater

The Sasirangan wastewater analyzed contained a COD of 276.9 mg/L and turbidity of 676 NTU, both far exceeding the Indonesian discharge standards (Ministry of Environment Regulation No. 5/2014). These baseline values highlight the urgent need for effective and low-cost treatment technologies applicable to small-scale industries. Ariyani et al. (2023) evaluated the ability of chitosan-epichlorohydrin beads to reduce total dissolved solids and dye content. Ariyani et al. (2023) evaluated the ability of chitosan-epichlorohydrin beads to reduce total dissolved solids and dye content. In the earlier work, Ariyani et al., 2023 evaluated the ability of chitosan-epichlorohydrin beads to reduce TDS and dye content. Building on that foundation, this study directs attention to different but equally critical parameters: COD and turbidity, by employing chitosan-TPP macropore beads (Ariyani et al., 2023).


Table 1. The results of the analysis of COD and turbidity of the Sasirangan wastewater samples

No.	Parameter	Method	Score
1	COD	The dichromate titrimetric	276,9 mg/L
2	Turbidity	The nephelometric	676 NTU

COD reflects the overall organic load, encompassing both biodegradable and recalcitrant compounds, whereas turbidity represents suspended solids and dye particulates. These indicators are directly related to ecological impacts and are particularly relevant for small-scale textile industries, where cost-effective treatment remains challenging. Thus, this study expands the scope of previous research by targeting more realistic indicators of wastewater quality.

3.2. Effect of Chitosan Dosage on COD Values

Figure 2 illustrates the effect of chitosan-TPP bead dosage on COD values in Sasirangan wastewater. Unexpectedly, a progressive increase in COD was observed with higher bead dosages. Rather than sequestering organic pollutants, the beads likely contributed additional oxidizable matter. This anomaly can be explained by partial bead disintegration during agitation and competitive interactions in wastewater. Ionic cross-linking between chitosan and TPP is relatively weak, and under treatment conditions, fragments of the polymer can leach into the solution. These fragments, containing hydroxyl and amine groups, are readily oxidized by potassium dichromate in COD titrimetric analysis, resulting in inflated COD values (Khubiev et al., 2023). Interestingly, the COD values in the untreated control decreased slightly, possibly due to self-coagulation and sedimentation of suspended solids. This contrast highlights that without stabilizing modifications, the application of chitosan-TPP beads may exacerbate the organic load rather than reduce it. Similar challenges have been documented for other weakly stabilized polysaccharide-based adsorbents (Rockson-Itiveh et al., 2024). Therefore, future strategies should prioritize enhancing bead structural integrity through dual cross-linking, incorporation of stabilizing fillers (e.g., silica, biochar), or immobilization in fixed matrices to ensure long-term stability and effective COD removal.

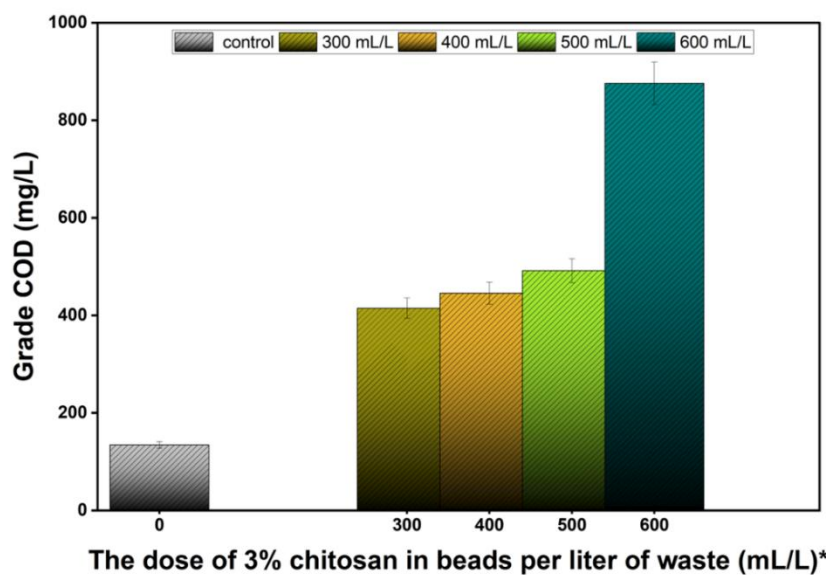

Desc: * chitosan dose = volume of chitosan solution used to make beads per 1 liter of sample

Figure 2. Effect of chitosan dose (3% chitosan in beads per liter of waste, mL/L) on COD values


3.3. Mechanistic Insight: Chitosan Oxidation and Bead Stability

The behavior of chitosan in aqueous environments is highly pH-dependent. In acidic media, the amine groups of chitosan are protonated ($-\text{NH}_2 \rightarrow -\text{NH}_3^+$), enhancing its solubility but also promoting stronger electrostatic interactions with TPP ions (Kurniasih et al., 2011). However, at neutral or basic pH, these groups deprotonate, weakening the ionic cross-links and promoting the release of chitosan. The dissolution of chitosan from beads under varying pH conditions directly contributed to elevated COD values, as the released polymer was readily oxidized. Thus, the integrity of chitosan-TPP beads is not solely a function of cross-linking efficiency but also of environmental pH and hydrodynamic conditions.

This finding calls for further research on bead reinforcement strategies, including dual cross-linking or hybrid composite formulations (e.g., chitosan-biochar or chitosan-silica composites), to ensure mechanical and chemical stability during application.

3.4. Effect of Chitosan Dosage on Turbidity Reduction

In contrast to COD, the turbidity of Sasirangan wastewater significantly decreased with increasing chitosan bead dosage, as shown in Figure 3. The most substantial reduction occurred at a 400 mL/L dosage, beyond which improvements plateaued. All treated samples met the turbidity standard (<50 NTU), indicating effective removal of suspended solids.

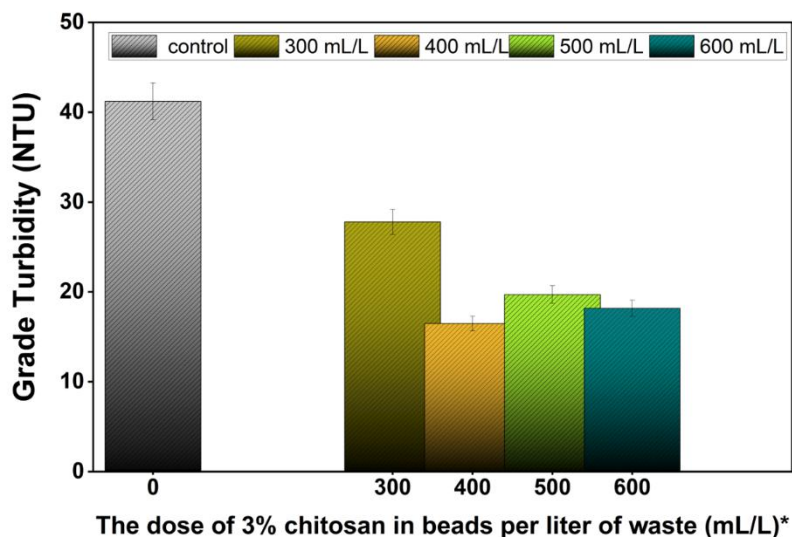

Desc: * chitosan dose = volume of chitosan solution used to make beads per 1 liter of sample

Figure 3. Effect of chitosan dose (3% chitosan in beads per liter of waste, mL/L) on turbidity values

The turbidity removal mechanism is likely to be dominated by a combination of physical entrapment, adsorption, and charge neutralization. The nature of cationic chitosan under acidic to neutral pH allows electrostatic interactions with negatively charged particles, whereas the porous bead structure enhanced by NaHCO_3 as a porogen facilitates the capture of colloids and dyes (Ariyani, Mujiyanti, Santoso, Irawati, et al., 2021; Chiou & Li, 2003). The large surface area offered by the macropores promotes bridging and floc formation, which subsequently settles or is filtered out. However, diminishing returns beyond 400 mL/L suggest that adsorption sites reach saturation, and excess beads may hinder optimal mixing or contribute to the redispersion of solids. This behavior aligns with Langmuir-type adsorption kinetics, in which monolayer coverage limits further uptake once equilibrium is reached.

3.5. Effect of pH on COD Values

Figure 4 illustrates the effect of the initial pH on COD values after treatment with chitosan-TPP beads. A clear trend was observed: COD values increased progressively as pH rose. A clear trend was observed: COD values increased progressively with increasing pH. Conversely, under neutral and alkaline conditions, deprotonation weakened electrostatic bonds, causing bead swelling, matrix disruption, and leaching of chitosan fragments (Figure 5-7). Conversely, under neutral and alkaline conditions, deprotonation weakened electrostatic bonds, causing bead swelling, matrix disruption, and leaching of chitosan fragments (Figure 5-7). These fragments, rich in hydroxyl and amine groups, are readily oxidized during dichromate titration, artificially inflating COD readings (Khubiev et al., 2023). Interestingly, at pH 3, COD reduction was only 1.01%, confirming that although acidic conditions prevent bead disintegration, the beads themselves lack sufficient capacity to reduce organic loads significantly. This highlights a fundamental limitation of ionic cross-linking systems, which are highly sensitive to pH. Similar findings have been reported in polysaccharide-based adsorbents under alkaline environments (Rockson-Itiveh et al., 2024). For practical applications, treatment under acidic pH is necessary, but to achieve effective COD removal, chitosan-TPP beads must be further reinforced such as through dual cross-linking, incorporation of inorganic fillers, or coupling with biological/oxidative post-treatment.

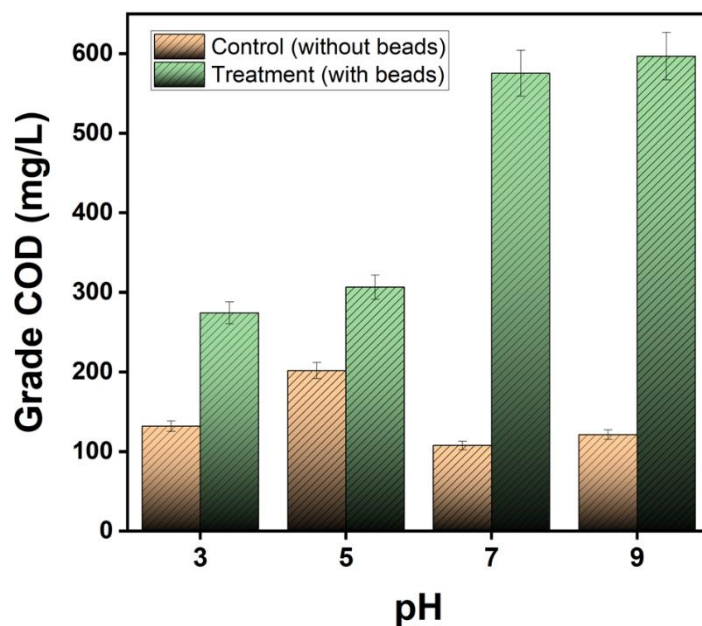


Figure 4. Effect of pH on the performance of macroporous beads in reducing COD values

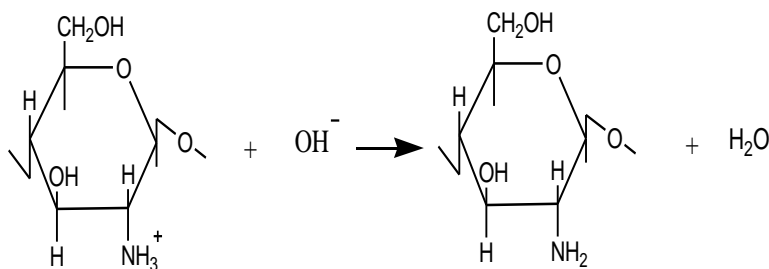


Figure 5. Deprotonation reaction beads of chitosan-TPP

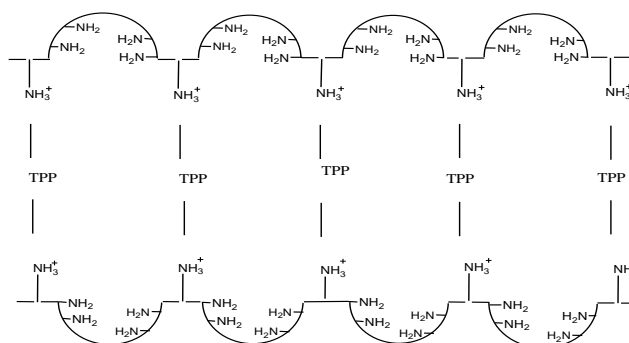


Figure 6. The shape loop of chitosan-TPP molecules due to cross-binding with TPP at basic pH

The alkaline conditions of the cross-links between chitosan and TPP ions result in a lower degree of release into the waste than under acidic conditions, as shown in Figure 7. The COD value only decreased at pH 3 by 1.01%, because at acidic pH, the cross-link density between chitosan and TPP ions can be maintained, preventing easy release into the waste. Under acidic conditions, the -NH₂ of chitosan is protonated to -NH₃⁺, resulting in a denser cross-linking interaction between the -NH₃⁺ of chitosan and the TPP ion. Based on the results of this study, beads are less effective in reducing the COD value in Sasirangan wastewater treatment. In contrast, the strong electrostatic interaction between protonated amines (-NH₃⁺) and TPP ions under acidic pH results in tighter cross-linking and a more robust bead

structure. This configuration restricts the release of chitosan into the surrounding medium, contributing to better COD control.

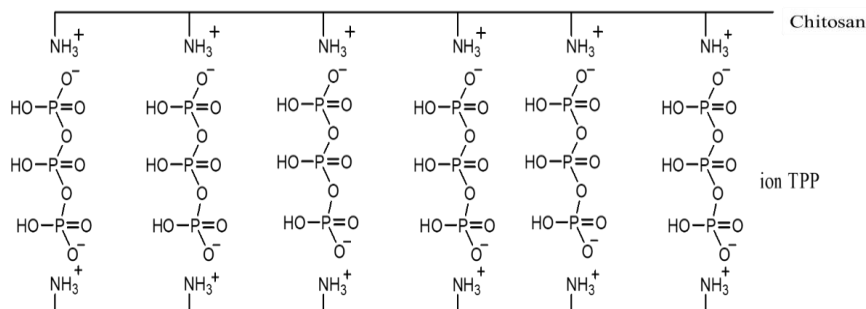


Figure 7. Cross-bond interaction between chitosan and TPP ions in an acidic solution.

3.6. Effect of pH on Turbidity Reduction

Figure 8 illustrates the influence of the initial pH (3, 5, 7, and 9) on the turbidity removal efficiency of chitosan–TPP beads. Interestingly, unlike COD, turbidity reduction was largely unaffected by pH variations. Across all conditions, turbidity decreased significantly, reaching values below the regulatory discharge standard (<50 NTU). This suggests that the dominant mechanisms for turbidity removal—namely, physical entrapment of suspended solids, flocculation, and adsorption within macroporous structures—are relatively insensitive to changes in surface charge (Annabi et al., 2010). The addition of NaHCO₃ as a porogen generated interconnected macropores that enhanced bead porosity, enabling the efficient capture of colloidal particles regardless of the protonation state. This observation is consistent with previous reports showing that structural features, rather than electrostatic interactions, govern turbidity reduction (Ibrahim, 2013). The robustness of performance across a wide pH range provides a practical advantage, as many small-scale textile producers cannot afford continuous pH adjustment. However, while turbidity removal was highly effective, in contrast to COD behavior, this underscores a critical limitation: the beads are efficient for particulate matter but inadequate for dissolved organics. This emphasizes the need for hybrid treatment systems in which chitosan–TPP beads serve as a pretreatment for turbidity, followed by biological or oxidative processes for COD reduction.

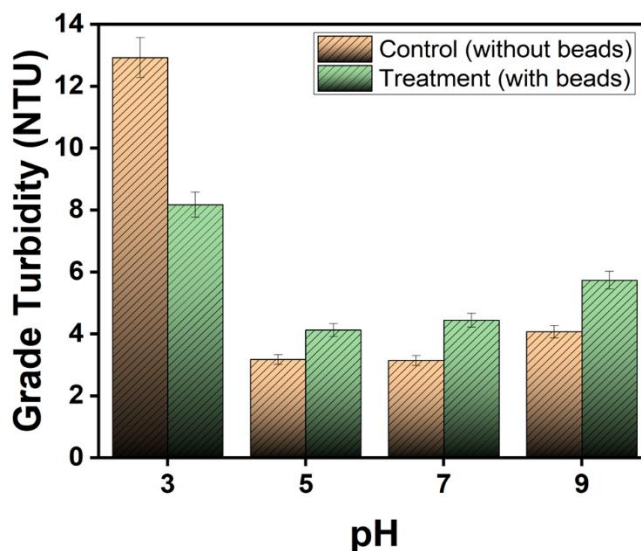


Figure 8. Effect of pH on the performance of macroporous beads in reducing turbidity values

3.7. Scanning Electron Microscopy (SEM) Analysis: Morphological Insights

SEM analysis (Figure 9) revealed critical insights into the morphological differences between beads synthesized with and without NaHCO_3 . The beads without a porogen appeared smooth and dense, offering limited surface area and pore accessibility. In contrast, the beads prepared with NaHCO_3 displayed rough, irregular textures with interconnected macropores, resulting from CO_2 release during bicarbonate decomposition (Anggraeny et al., 2014). These macropores play a central role in facilitating turbidity removal, as they increase the active surface area, enhance mass transfer, and enable the physical entrapment of suspended solids and dye aggregates. Therefore, the strong performance observed across all pH ranges for turbidity reduction (Figure 8) can be directly attributed to the structural porosity revealed in the SEM images.

However, the same porosity may also represent a weakness. Enlarged cavities reduce mechanical stability and render the matrix more susceptible to fragmentation during mixing or at alkaline pH. Thus, the SEM results validate the mechanism underlying efficient turbidity removal and explain the paradoxical increase in COD. This underscores the importance of balancing porosity and stability when designing chitosan-based adsorbents for real-world wastewater applications. This underscores the importance of balancing porosity and stability when designing chitosan-based adsorbents for real wastewater applications.

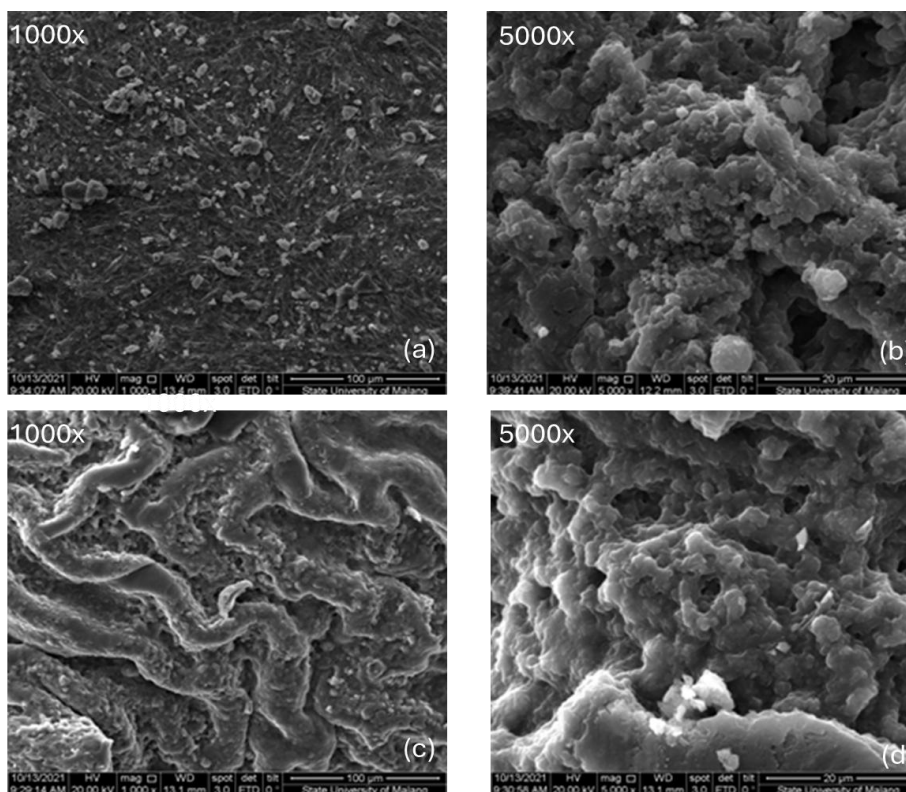


Figure 9. SEM Chitosan-TPP beads : (a) without NaHCO_3 , magnification 1000x, (b) without NaHCO_3 , magnification 5000x, (c) with NaHCO_3 , magnification 1000x and (d) with NaHCO_3 , magnification 5000x

3.8. Fourier Transform Infrared Spectroscopy (FTIR) Analysis: Chemical Interaction Evidence

FTIR analysis (Figure 10; Table 2) provided further evidence of the adsorption mechanisms. Compared to the spectra of the pristine beads, those exposed to Sasirangan wastewater exhibited several distinct changes. A new absorption peak at 1606 cm^{-1} corresponded to azo groups ($-\text{N}=\text{N}-$), confirming that dye molecules from the wastewater were successfully adsorbed onto the chitosan-TPP surface. Additionally, shifts in the OH/NH stretching regions ($3317\text{--}3624\text{ cm}^{-1}$) suggested strong hydrogen

bonding and electrostatic interactions between bead functional groups and the polar groups of organic contaminants. Aliphatic C-H vibrations and C-O-C stretching shifts also indicated Van der Waals and ionic interactions with dyes and organic molecules (Vakili et al., 2014; Zhao et al., 2016).

These findings highlight the dual functionality of the beads: physical entrapment via macropores (validated by SEM) and chemical adsorption via surface functional groups. This synergy explains the efficient turbidity removal observed at all pH values. However, the persistence of elevated COD values suggests that while dyes were bound, soluble chitosan fragments released into solution also contributed to the oxidizable organic load. Thus, FTIR results complement COD-turbidity findings, emphasizing both the strengths (effective dye adsorption) and limitations (polymer leaching) of the chitosan-TPP bead system.

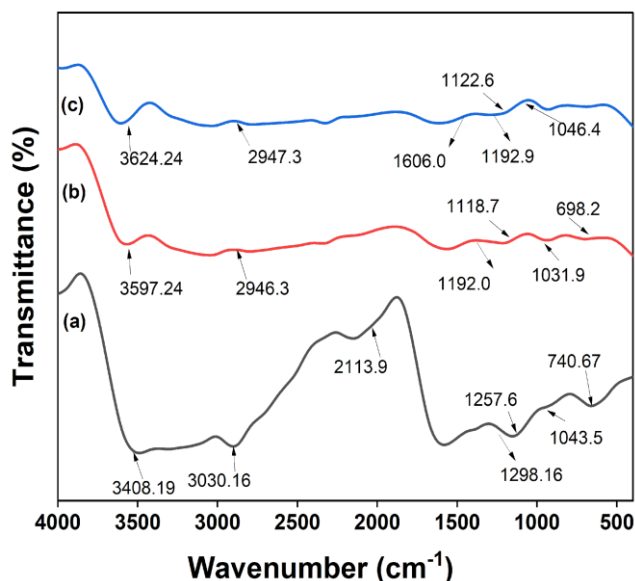


Figure 10. Spectra FTIR chitosan (a), beads chitosan (b), beads+chitosan+waste (c)

Table 2. Identification of each functional group in the infrared spectrum of chitosan, beads chitosan-TPP beads, and beads chitosan-TPP with waste

Chitosan (cm ⁻¹)	Beads chitosan-TPP (cm ⁻¹)	Beads chitosan-TPP + waste (cm ⁻¹)	Identity
740.67	698.23		Stretching vibration 1,4-glycosidic
898.83			C-O-C Vibration
1043.49	1031.92	1046.,41	Symmetric stretching vibration C-O
1257.59	1118.71	1122.57	
1298.16	1192.01	1195.87	
		1224.80	
	2113.98		Vibration C-H aromatic
	2237.43		
		1606,01	-N=N-
3030.16	2946.30	2889.37	Aliphatic C -H
3089.98		2947.23	Vibration
3317.56	3597.24	3624.24	O-H vibration overlap
3408.19			N-H vibration

3.9. Synthesis of Findings and Implications for Practice

The study of chitosan-TPP (tripolyphosphate) macroporous beads in the treatment of textile wastewater reveals significant insights into their efficacy and limitations in managing the complex nature of textile effluents. Notably, these beads demonstrated remarkable performance in turbidity removal, achieving reductions from 676 NTU to below 50 NTU, translating to an efficiency exceeding 95% at an optimal dosage of 400 mL/L. Such performance underscores the effectiveness of physical mechanisms, including flocculation and chemical adsorption, reinforced by the porosity induced from the incorporation of sodium bicarbonate (NaHCO_3), which enhanced the active surface areas and diffusion pathways essential for effective contaminant capture (Wahba, 2017).

Further analysis using scanning electron microscopy (SEM) and Fourier-transform infrared spectroscopy (FTIR) confirmed the dual mechanisms at play, illustrating both the physical entrapment of dye molecules and the presence of organic functional groups indicative of chemical interactions. However, the performance regarding chemical oxygen demand (COD) was paradoxically counterproductive; increases in COD at higher dosages and alkaline pH levels suggest instability in the chitosan bead structure, leading to the leaching of oxidizable fragments and complicating treatment outcomes (Zhang et al., 2024). This indicates a critical challenge within polysaccharide-based adsorbents: enhancing porosity and adsorptive capacity may concurrently compromise structural integrity, necessitating careful optimization in their application.

Practically, the effectiveness of chitosan-TPP beads suggests their potential as a pretreatment step within decentralized textile wastewater management systems, primarily aimed at rapid turbidity and color reduction. This method could complement subsequent biological or advanced oxidation treatments targeting dissolved organics, thereby improving overall treatment efficacy. Previous studies have highlighted similar incongruities in treatment efficiencies and structural stability when utilizing polysaccharide-based solutions, emphasizing the necessity for strategic reinforcements, such as dual cross-linking. Ultimately, for chitosan-TPP beads to transition into practical applications, enhancements such as immobilization within fixed matrices or integration with biochar or silica may be critical to mitigate issues related to polymer leaching while delivering sustained performance in low-cost and eco-friendly textile waste management solutions.

4. Conclusion

The application of macroporous chitosan-TPP beads in Sasirangan wastewater treatment demonstrated contrasting outcomes: while the beads effectively reduced turbidity, they contributed to an increase in COD. At an optimal dosage of 400 mL/L, turbidity was reduced from 676 NTU to 29.3 NTU, achieving a 95.7% removal efficiency and meeting discharge standards. However, COD values increased with higher bead dosages and rising pH, reaching a maximum of 366.5 mg/L at pH 9, which was approximately 32% higher than the initial COD of 276.9 mg/L. This increase is attributed to the dissolution of chitosan fragments into the solution due to weakened cross-linking under alkaline conditions, which contributed additional oxidizable organic matter. Despite this limitation, pH variation had minimal effects on turbidity removal, suggesting that flocculation and physical entrapment dominated the process. SEM analysis confirmed the role of NaHCO_3 in enhancing bead porosity, whereas FTIR spectra revealed the successful adsorption of dyes and organic compounds through interactions with functional groups in the chitosan matrix. Overall, although chitosan-TPP beads show promise for turbidity reduction in textile effluents, their use for COD removal requires further optimization to improve structural stability and minimize organic leaching.

Acknowledgement

The authors would like to thank Lambung Mangkurat University for funding this research through the Lambung Mangkurat University PNBP Financing Scheme for the 2021 Fiscal Year, MADYA Cluster, under

Research Implementation Agreement number: 009.30/UN8.2/PL/2021. The authors would also like to thank the Chemical Biomaterials Laboratory, FMIPA ULM, for providing the facilities necessary to conduct this research.

Ethic Statement

Ethical approval was not required for this study because it did not involve human participants or animals. The research was conducted using wastewater samples collected from textile industry effluents.

CRedit Author Statement

Dahlana Ariyani: Idea Development, Research Design, Project Administration, Supervision. **Riana Maulana:** Resources, Investigation, Manuscript Draft Preparation. **Utami Irawati:** Writing-Review. **Dwi Rasy Mujiyanti:** Visualization, Writing-Review. **Dewi Umaningrum:** Writing-Review.

References

- Annabi N., Nichol J.W., Zhong X., Ji C., Koshy S., Khademhosseini A., and Dehghani F. 2010. Controlling the porosity and microarchitecture of hydrogels for tissue engineering. *Tissue Engineering Part B: Reviews* 16, 371-383.
- Anggraeny B.O.D., Sabarudin A., and Rumhayati B. 2014. Pembuatan kitosan makropori menggunakan garam dapur dan aplikasinya terhadap adsorpsi methyl orange. *Jurnal Ilmu Kimia Universitas Brawijaya* 1, 1-7.
- Ariyani D., Mujiyanti D.R., Santoso U.T., Irawati U., Maulana R., and Rohmah R.E. 2021. Effect of chitosan concentration on macroporous chitosan-TPP beads toward turbidity, dye content, and COD of sasirangan wastewater. *Jurnal Kimia dan Pendidikan Kimia* 6, 264-273.
- Askia J., Ariyani D., and Santoso U.T. 2021. Sintesis beads kitosan terikat-silang tripolifosfat dengan penambahan porogen untuk adsorpsi asam humat. *Jurnal Sains dan Terapan Kimia* 15, 64-73.
- Bratby J. 2016. *Coagulation and flocculation in water and wastewater treatment.* IWA Publishing.
- Chiou M.S. and Li H.Y. 2003. Adsorption behavior of reactive dye in aqueous solution on chemical cross-linked chitosan beads. *Chemosphere* 50, 1095-1105.
- Ibrahim S.B. 2013. Turbidity measurement using an optical tomography system. *International Journal of Science and Engineering* 5, 66-72.
- Khair A. and Noraida N. 2025. The ability of alum to reduce color in sasirangan home industry wastewater. *Medical Laboratory Technology Journal* 11, 1-9.
- Khubiev O.M., Egorov A.R., Kirichuk A.A., Khrustalev V.N., Tskhovrebov A.G., and Kritchenkov A.S. 2023. Chitosan-based antibacterial films for biomedical and food applications. *International Journal of Molecular Sciences* 24, 10738.
- Kurniasih M., Aprilita N., and Kartini I. 2011. Sintesis dan karakterisasi crosslink kitosan dengan tripolifosfat pH 3. *Molekul* 6, 19-24.
- Mi F.L., Sung H.W., Shyu S.S., Su C.C., and Peng C.K. 2003. Synthesis and characterization of biodegradable TPP/genipin co-crosslinked chitosan gel beads. *Polymer* 44, 6521-6530.
- Nidheesh P. and Gandhimathi R. 2012. Trends in electro-Fenton process for water and wastewater treatment: an overview. *Desalination* 299, 1-15.
- Nooryaneti M., Tuhuloula A., and Irawan C. 2023. Phytoremediation using water hyacinth for sasirangan wastewater treatment. *Toward Adaptive Research and Technology Development for Future Life* 2689, 060006.
- Nunes P., Roland F., Amado A.M., Resende N.S., and Cardoso S.J. 2022. Responses of planktonic chlorophyll-a composition to inorganic turbidity caused by mine tailings. *Frontiers in Environmental Science* 9, 605838.
- Nurmasari R., Umaningrum D., and Yuliyanti E. 2018. Kajian sorpsi zat warna safranin o pada sorben beads kitosan-tripolifosfat. *Jurnal Sains dan Terapan Kimia* 12, 34-40.

- Oturan M.A. and Aaron J.J. 2014. Advanced oxidation processes in water/wastewater treatment: principles and applications. A review. *Critical Reviews in Environmental Science and Technology* 44, 2577-2641.
- Ravi Kumar M.N.V.R. 2000. A review of chitin and chitosan applications. *Reactive and Functional Polymers* 46, 1-27.
- Robinson T., McMullan G., Marchant R., and Nigam P. 2001. Remediation of dyes in textile effluent: a critical review on current treatment technologies with a proposed alternative. *Bioresource Technology* 77, 247-255.
- Rockson-Itiwah D., Chidiebere F., and Keke M. 2024. The use of chitosan as a coagulant in wastewater treatment. *International Journal of Environmental Pollution and Environmental Modelling* 7, 27-36.
- Sahoo D. and Anandhi A. 2023. Conceptualizing turbidity for aquatic ecosystems in the context of sustainable development. *Environmental Science: Advances* 2, 1220-1234.
- Syauqiah I., Amalia M., and Kartini H.A. 2011. Analisis variasi waktu dan kecepatan pengaduk pada proses adsorpsi limbah logam berat dengan arang aktif. *Informasi-Teknik* 12, 11-20.
- Utami U.B.L. and Nurmasari R. 2012. Pengolahan limbah cair sasirangan secara filtrasi melalui pemanfaatan arang kayu ulin sebagai adsorben. *Jurnal Sains MIPA Universitas Lampung* 13, 190-196.
- Vakili M., Rafatullah M., Salamatinia B., Abdullah A.Z., Ibrahim M.H., Tan K.B., Gholami Z., and Amouzgar P. 2014. Application of chitosan and its derivatives as adsorbents for dye removal from water and wastewater: a review. *Carbohydrate Polymers* 113, 115-130.
- Verma A.K., Dash R.R., and Bhunia P. 2012. A review on chemical coagulation/flocculation technologies for removal of colour from textile wastewaters. *Journal of Environmental Management* 93, 154-168.
- Zhao P., Xin M., Li M., and Deng J. 2016. Adsorption of methyl orange from aqueous solution using β -cyclodextrin modified chitosan microspheres. *Desalination and Water Treatment* 57, 11850-11858